

**\*MAT\_162  
\*MAT\_COMPOSITE\_MSC\_DMG**

# **A PROGRESSIVE COMPOSITE DAMAGE MODEL FOR UNIDIRECTIONAL AND WOVEN FABRIC COMPOSITES**

**UD-CCM Updates on MAT162 USER MANUAL  
Version 17A-2017**

Materials Sciences Corporation (MSC)  
&  
University of Delaware Center for Composite Materials (UD-CCM)

**May 2017**

Technical Support  
**Bazle Z. (Gama) Haque, PhD**  
Senior Scientist, University of Delaware Center for Composite Materials (UD-CCM)  
Assistant Professor, Department of Mechanical Engineering, University of Delaware  
Newark, DE 19716. Tel: (302) 831-6805, Cell: (302) 690-4741  
E-mail: [gama@udel.edu](mailto:gama@udel.edu) Web: <http://www.ccm.udel.edu/software/mat162/>

© University of Delaware Center for Composite Materials. All Rights Reserved.

**Types of MAT162 licenses include: Educational, Commercial, and 30-Day Trial (US only).  
License Agreement required to be signed prior to activation of MAT161/162.  
Licenses include User's Manual and Technical Support.  
For More Information: Call MSC (215)542-8400 or email [dyna\\_161@materials-sciences.com](mailto:dyna_161@materials-sciences.com)**

This Page is Intentionally Left Blank

**\*MAT\_COMPOSITE\_MSC\_{OPTION}**

Available options include:

<BLANK>

**DMG**

These are Material Types 161 and 162. These material types may be used to model the progressive failure in composite materials consisting of unidirectional and woven fabric layers subjected to high strain-rate and high pressure loading conditions. The progressive layers failure criteria have been established by adopting the methodology developed by Hashin [1980] with a generalization to include the effect of highly constrained pressure on composite failure. These failure models can be used to effectively simulate fiber failure, matrix damage, and delamination behavior under all conditions – opening, closure, and sliding of failure surfaces. The model with DMG option (material 162) is a generalization of the basic layer failure model of Material 161 by adopting the damage mechanics approach [Matzenmiller et al., 1995] for characterizing the softening behavior after damage initiation. These models require an additional license from Materials Sciences Corporation, which developed and supports these models in collaboration with University of Delaware Center for Composite Materials (UD-CCM).

Card 1	1	2	3	4	5	6	7	8
Variable	MID	RO	EA	EB	EC	PRBA	PRCA	PRCB
Type	A8	F	F	F	F	F	F	F

Card 2	1	2	3	4	5	6	7	8
Variable	GAB	GBC	GCA	AOPT	MACF			
Type	F	F	F	F	I			

Card 3	1	2	3	4	5	6	7	8
Variable	XP	YP	ZP	A1	A2	A3		
Type	F	F	F	F	F	F		

Card 4	1	2	3	4	5	6	7	8
Variable	V1	V2	V3	D1	D2	D3	BETA	
Type	F	F	F	F	F	F	F	

Card 5	1	2	3	4	5	6	7	8
Variable	SAT	SAC	SBT	SBC	SCT	SFC	SFS	S_AB
Type	F	F	F	F	F	F	F	F

Card 6	1	2	3	4	5	6	7	8
Variable	S_BC	S_CA	SFFC	AMODEL	PHIC	E_LIMT	S_DELM	
Type	F	F	F	F	F	F	F	

Card 7	1	2	3	4	5	6	7	8
Variable	OMGMX	ECRSH	EEXPXN	CERATE1	AM1			
Type	F	F	F	F	F			

Define the following card if and only if the option DMG is specified.

Card 8	1	2	3	4	5	6	7	8
Variable	AM2	AM3	AM4	CERATE2	CERATE3	CERATE4		
Type	F	F	F	F	F	F		

**VARIABLE****DESCRIPTION**

MID	Material identification. A unique number or label not exceeding 8 characters must be specified.
RO	Mass density
EA	$E_a$ , Young's modulus - longitudinal direction♥
EB	$E_b$ , Young's modulus - transverse direction♥
EC	$E_c$ , Young's modulus – through thickness direction♥
PRBA	$\nu_{ba}$ , Poisson's ratio ba
PRCA	$\nu_{ca}$ , Poisson's ratio ca
PRCB	$\nu_{cb}$ , Poisson's ratio cb
GAB	$G_{ab}$ , shear modulus ab
GBC	$G_{bc}$ , shear modulus bc
GCA	$G_{ca}$ , shear modulus ca

♥ LS-DYNA® notations a, b, & c have the same meaning as for orthotropic material axes notations 1, 2, & 3.


<u>VARIABLE</u>	<u>DESCRIPTION</u>
AOPT	<p>Material axes option, see Figure 2.1. (in KEYWORD Manual)</p> <p><b>EQ.0.0:</b> locally orthotropic with material axes determined by element nodes as shown in Figure 2.1. Nodes 1, 2, and 4 of an element are identical to the Nodes used for the definition of a coordinate system by *DEFINE_COORDINATE_NODES.</p> <p><b>EQ.1.0:</b> locally orthotropic with material axes determined by a point in space and the global location of the element center, this is the a-direction.</p> <p><b>EQ.2.0:</b> globally orthotropic with material axes determined by vectors defined below, as with *DEFINE_COORDINATE_VECTOR.</p> <p><b>LT.0.0:</b> the absolute value of AOPT is a coordinate system ID number (CID on *DEFINE_COORDINATE_NODES, *DEFINE_COORDINATE_SYSTEM or *DEFINE_COORDINATE_VECTOR). Available in R3 version of 971 and later.</p>
MACF	<p>Material axes change flag:</p> <p>EQ.1: No change, default,</p> <p>EQ.2: switch material axes a &amp; b,</p> <p>EQ.3: switch material axes a &amp; c,</p> <p>EQ.4: switch material axes b &amp; c.</p>
XP YP ZP	Define coordinates of point <b>p</b> for AOPT = 1.
A1 A2 A3	Define components of vector <b>a</b> for AOPT = 2.
V1 V2 V3	Define components of vector <b>v</b> for AOPT = 3.
D1 D2 D3	Define components of vector <b>d</b> for AOPT = 2.
BETA	Layer in-plane rotational angle in degrees.
SAT	Longitudinal tensile strength, $S_{aT}$
SAC	Longitudinal compressive strength, $S_{aC}$
SBT	Transverse tensile strength, $S_{bT}$
SBC	Transverse compressive strength, $S_{bC}$
SCT	Through thickness tensile strength, $S_{cT}$
SFC	Crush strength, $S_{FC}$
SFS	Fiber mode shear strength, $S_{FS}$

<u>VARIABLE</u>	<u>DESCRIPTION</u>
S_AB♦	Matrix mode shear strength, ab plane, see below, $S_{ab}$
S_BC♦	Matrix mode shear strength, bc plane, see below, $S_{bc}$
S_CA♦	Matrix mode shear strength, ca plane, see below, $S_{ca}$
SFFC	Scale factor for residual compressive strength, $S_{FFC}$
AMODEL	Material models: EQ.1: Unidirectional lamina model EQ.2: Fabric lamina model
PHIC	Coulomb friction angle for matrix and delamination failure, $\varphi < 90^\circ$
S_DELM	Scale factor for delamination criterion, $S$
OMGMX	Limit damage parameter for elastic modulus reduction, $\bar{w}_{max}$
E_LIMT	Element eroding axial strain
ECRSH	Limit compressive relative volume for element eroding
EEXPN	Limit expansive relative volume for element eroding
CERATE1	Coefficient for strain rate dependent strength properties, $C_{rate1}$
CERATE2	Coefficient for strain rate dependent axial moduli, $C_{rate2}$
CERATE3	Coefficient for strain rate dependent shear moduli, $C_{rate3}$
CERATE4	Coefficient for strain rate dependent transverse moduli, $C_{rate4}$
AM1	Coefficient for strain softening property for fiber damage in a direction, $m_1$
AM2	Coefficient for strain softening property for transverse compressive matrix failure mode in b direction (unidirectional) or for fiber damage mode in b direction (fabric), $m_2$
AM3	Coefficient for strain softening property for fiber crush and punch shear damage, $m_3$
AM4	Coefficient for strain softening property for matrix failure and delamination damage, $m_4$

---

♦ LS-DYNA KEYWORD manual presents these parameters as: SAB, SBC, & SCA. Since SBC is also used to define the “transverse compressive strength,” we have used S\_xx to represent shear strength in xx plane.


Figure 2.1. from the KEYWORD Manual of LS-DYNA® is reproduced here for the convenience of the MAT162 users.

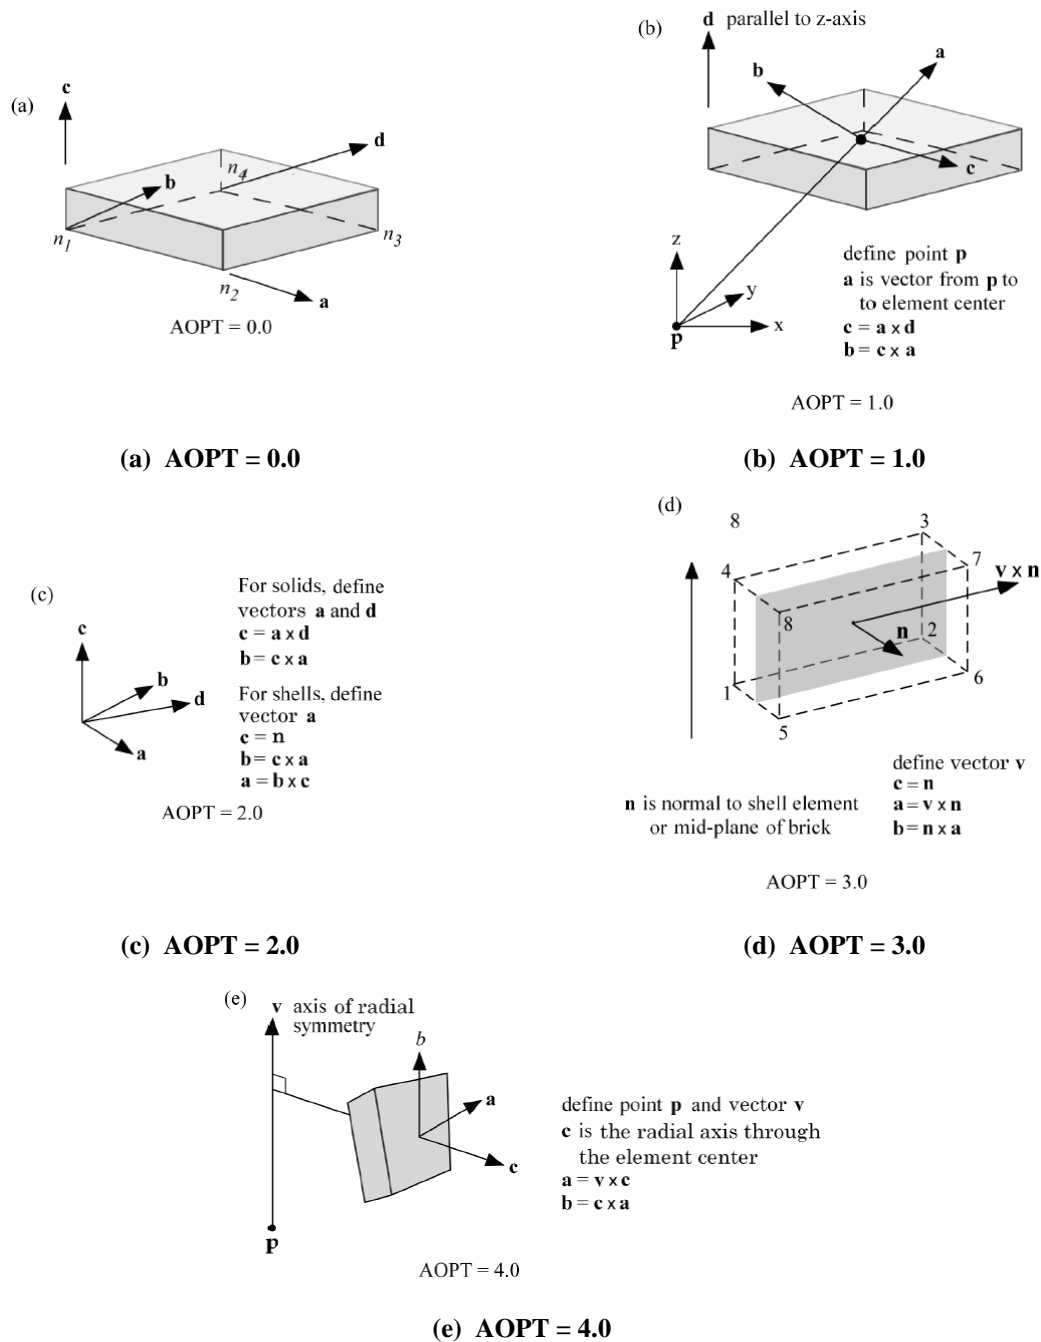


**Figure 2.1.** Options for determining principal material axes: (a) AOPT = 0.0, (b) AOPT = 1.0 for brick elements, (c) AOPT = 2.0, (d) AOPT = 3.0, and (e) AOPT=4.0 for brick elements.

**Figure 1: Material Axes Definition presented in the LS-DYNA KEYWORD Manual (OLDER VERSIONS)**


**AOPT = 0.0**

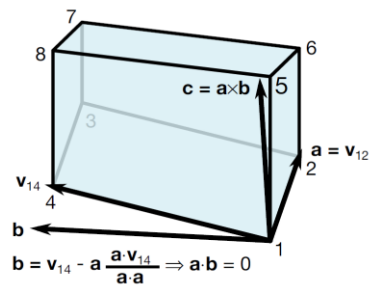


**AOPT = 1.0**

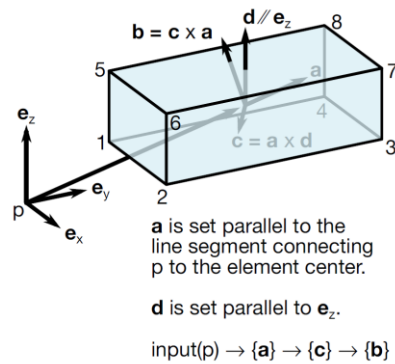


**AOPT = 2.0 (solid)**

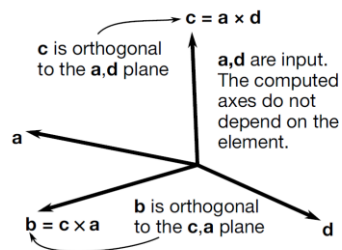


**AOPT = 2.0 (shell)**

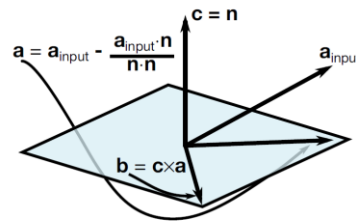

**AOPT = 3.0**

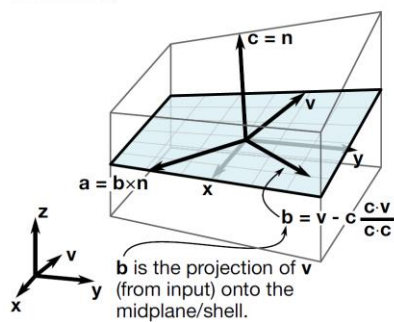

**AOPT = 4.0**

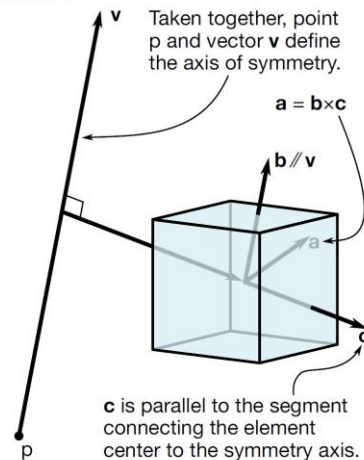

**Figure 1 (Continued): Material Axes Definition presented in the LS-DYNA Manuals (NEW VERSIONS, May 2014)**



## MATERIAL MODELS

Failure models based on the 3D stresses/strains in a composite lamina with improved progressive failure modeling capability are established for a unidirectional and for a fabric composite lamina. **While the LS-DYNA KEYWORD manual presents the stress based formulations, this manual presents the strain based formulations.** These models can be used to effectively simulate the fiber failure, matrix failure, and delamination behavior of composites under high strain-rate and high pressure ballistic impact conditions.

The unidirectional and fabric lamina failure criteria and the associated property degradation models are described as follows. All the failure criteria are expressed in terms of stress components based on ply level strains  $(\varepsilon_1, \varepsilon_2, \varepsilon_3, \varepsilon_{12}, \varepsilon_{23}, \varepsilon_{31}) = (\varepsilon_a, \varepsilon_b, \varepsilon_c, \varepsilon_{ab}, \varepsilon_{bc}, \varepsilon_{ca})$ . The associated elastic moduli are  $(E_1, E_2, E_3, G_{12}, G_{23}, G_{31}) = (E_a, E_b, E_c, G_{ab}, G_{bc}, G_{ca})$ . Note that for the unidirectional model, a, b, and c denote the fiber, in-plane transverse and out-of-plane or through-thickness directions, respectively; while for the fabric model, a, b, and c denote the in-plane fill, in-plane warp and out-of-plane or through-thickness directions, respectively.

## UNIDIRECTIONAL LAMINA DAMAGE MODEL

### Fiber Mode Failures

The fiber failure criteria of Hashin [1980] for a unidirectional layer are generalized to characterize the fiber damage in terms of strain components for a unidirectional layer. Three damage functions are used for fiber failure, one in tension/shear, one in compression, and another one in crush under pressure. They are chosen in terms of quadratic strain forms as follows:

TENSION-SHEAR FIBER MODE: MODE 1u

$$f_1 - r_1^2 = \left( \frac{E_a \langle \varepsilon_a \rangle}{S_{aT}} \right)^2 + \left( \frac{G_{ab}^2 \varepsilon_{ab}^2 + G_{ca}^2 \varepsilon_{ca}^2}{S_{FS}^2} \right) - r_1^2 = 0 \quad (1)$$

COMPRESSION FIBER MODE: MODE 2u

$$f_2 - r_2^2 = \left( \frac{E_a \langle \varepsilon_a' \rangle}{S_{aC}} \right)^2 - r_2^2 = 0, \rightarrow \varepsilon_a' = -\varepsilon_a - \frac{\langle -E_c \varepsilon_c - E_b \varepsilon_b \rangle}{2E_a} \quad (2)$$

CRUSH MODE: MODE 3u

$$f_3 - r_3^2 = \left( \frac{E_c \langle -\varepsilon_c \rangle}{S_{FC}} \right)^2 - r_3^2 = 0 \quad (3)$$

where  $\langle \rangle$  are Macaulay brackets,  $S_{aT}$  and  $S_{aC}$  are the tensile and compressive strengths in the fiber direction, and  $S_{FS}$  and  $S_{FC}$  are the layer strengths associated with the fiber shear and crush failure, respectively. The damage thresholds,  $r_j$ ,  $j = 1, 2, 3$ , have the initial values equal to 1 before the damage initiated, and are updated due to damage accumulation in the associated damage modes.

### Matrix Mode Failures

Matrix mode failures must occur without fiber failure, and hence they will be on planes parallel to fibers. Two matrix damage functions are chosen for the failure plane perpendicular and parallel to the layering planes. They have the forms:

TRANSVERSE COMPRESSIVE MATRIX MODE: MODE 4u

$$f_4 - r_4^2 = \left( \frac{E_b \langle -\varepsilon_b \rangle}{S_{bC}} \right)^2 - r_4^2 = 0 \quad (4)$$

PERPENDICULAR MATRIX MODE: MODE 5u

$$f_5 - r_5^2 = \left( \frac{E_b \langle \varepsilon_b \rangle}{S_{bT}} \right)^2 + \left( \frac{G_{bc} \varepsilon_{bc}}{S_{bc0} + S_{SRB}} \right)^2 + \left( \frac{G_{ab} \varepsilon_{ab}}{S_{ab0} + S_{SRB}} \right)^2 - r_5^2 = 0 \quad (5)$$

PARALLEL MATRIX MODE (DELAMINATION): MODE 6u

$$f_6 - r_6^2 = S^2 \left\{ \left( \frac{E_c \langle \varepsilon_c \rangle}{S_{cT}} \right)^2 + \left( \frac{G_{bc} \varepsilon_{bc}}{S_{bc0} + S_{SRC}} \right)^2 + \left( \frac{G_{ca} \varepsilon_{ca}}{S_{ca0} + S_{SRC}} \right)^2 \right\} - r_6^2 = 0 \quad (6)$$

where  $S_{bT}$  and  $S_{cT}$  are the transverse tensile strengths of the corresponding tensile modes ( $\varepsilon_b > 0$  or  $\varepsilon_c > 0$ ); and  $S_{ab0}$ ,  $S_{bc0}$ , &  $S_{ca0}$  are the quasi-static shear strength values. Under compressive transverse strain,  $\varepsilon_b < 0$  or  $\varepsilon_c < 0$ , the damaged surface is considered to be “closed”, and the shear strengths are assumed to depend on the compressive normal strains based on the Mohr-Coulomb theory, i.e.:

$$\begin{aligned} S_{SRB} &= E_b \tan(\varphi) \langle -\varepsilon_b \rangle \\ S_{SRC} &= E_c \tan(\varphi) \langle -\varepsilon_c \rangle \end{aligned} \quad (7)$$

where  $\varphi$  is a material constant as  $\tan(\varphi)$  is similar to the coefficient of friction. The damage thresholds  $r_j$ ,  $j = 4, 5, 6$ , have the initial values equal to 1 before the damage initiated, and are updated due to damage accumulation of the associated damage modes.

Failure predicted by the criterion of  $f_4$  and  $f_5$  can be referred to as transverse matrix failure, while the matrix failure predicted by  $f_6$ , which is parallel to the layer, can be referred as the delamination mode when it occurs within the elements that are adjacent to the ply interface. Note that a scale factor  $S$  is introduced to provide better correlation of delamination area with experiments. The scale factor  $S$  can be determined by fitting the analytical prediction to experimental data for the delamination area.

## FABRIC LAMINA DAMAGE MODEL

### *Fiber Mode Failures*

The fiber failure criteria of Hashin [1980] for a unidirectional layer are generalized to characterize the fiber damage in terms of strain components for a plain weave layer. The fill and warp fiber tensile/shear damage are given by the quadratic interaction between the associated axial and through the thickness shear strains, i.e.:

TENSION-SHEAR FIBER MODES: MODE 1f & 2f

$$\begin{aligned} f_7 - r_7^2 &= \left( \frac{E_a \langle \varepsilon_a \rangle}{S_{aT}} \right)^2 + \left( \frac{G_{ca} \varepsilon_{ca}}{S_{aFS}} \right)^2 - r_7^2 = 0 \\ f_8 - r_8^2 &= \left( \frac{E_b \langle \varepsilon_b \rangle}{S_{bT}} \right)^2 + \left( \frac{G_{bc} \varepsilon_{bc}}{S_{bFS}} \right)^2 - r_8^2 = 0 \end{aligned} \quad (8)$$

where  $S_{aT}$  and  $S_{bT}$  are the axial tensile strengths in the fill and warp directions, respectively, and  $S_{aFS}$  and  $S_{bFS}$  are the lamina shear strengths due to fiber shear failure in the fill and warp directions. These failure criteria are applicable when the associated  $\varepsilon_a$  or  $\varepsilon_b$  is positive. The damage thresholds  $r_7$  and  $r_8$  are equal to 1 without damage. It is assumed  $S_{aFS} = S_{FS}$ , and  $S_{bFS} = S_{FS} \times S_{bT} / S_{aT}$ .

COMPRESSION FIBER MODES: MODE 3f & 4f

When  $\varepsilon_a$  or  $\varepsilon_b$  is compressive, it is assumed that the in-plane compressive damage in the fill and warp directions are given by the maximum strain criterion, i.e.:

$$\begin{aligned} f_9 - r_9^2 &= \left( \frac{E_a \langle \varepsilon'_a \rangle}{S_{aC}} \right)^2 - r_9^2 = 0 & \rightarrow & \varepsilon'_a = -\varepsilon_a - \langle -\varepsilon_c \rangle \frac{E_c}{E_a} \\ f_{10} - r_{10}^2 &= \left( \frac{E_b \langle \varepsilon'_b \rangle}{S_{bC}} \right)^2 - r_{10}^2 = 0 & \rightarrow & \varepsilon'_b = -\varepsilon_b - \langle -\varepsilon_c \rangle \frac{E_c}{E_b} \end{aligned} \quad (9)$$

where  $S_{aC}$  and  $S_{bC}$  are the axial compressive strengths in the fill and warp directions, respectively, and  $r_9$  and  $r_{10}$  are the corresponding damage thresholds. Note that the effect of through the thickness compressive strain on the in-plane compressive damage is taken into account in the above two equations.

#### CRUSH MODE: MODE 5f

When a composite material is subjected to transverse impact by a projectile, high compressive stresses will generally occur in the impact area with high shear stresses in the surrounding area between the projectile and the target material. While the fiber shear punch damage due to the high shear stresses can be accounted for by equation (1), the crush damage due to the high through the thickness compressive pressure is modeled using the following criterion:

$$f_{11} - r_{11}^2 = \left( \frac{E_c \langle -\varepsilon_c \rangle}{S_{FC}} \right)^2 - r_{11}^2 = 0 \quad (10)$$

where  $S_{FC}$  is the fiber crush strengths and  $r_{11}$  is the associated damage threshold.

#### Matrix Mode Failures

##### IN-PLANE MATRIX MODE: MODE 6f

A plain weave layer can be damaged under in-plane shear stressing without occurrence of fiber breakage. This in-plane matrix damage mode is given by:

$$f_{12} - r_{12}^2 = \left( \frac{G_{ab} \varepsilon_{ab}}{S_{ab}} \right)^2 - r_{12}^2 = 0 \quad (11)$$

where  $S_{ab}$  is the layer shear strength due to matrix shear failure and  $r_{12}$  is the damage threshold.

##### PARALLEL MATRIX MODE (DELAMINATION): MODE 7f

Another failure mode, which is due to the quadratic interaction between the transverse strains, is expected to be mainly a matrix failure. This through the thickness matrix failure criterion is assumed to have the following form:

$$f_{13} - r_{13}^2 = S^2 \left\{ \left( \frac{E_c \langle \varepsilon_c \rangle}{S_{cT}} \right)^2 + \left( \frac{G_{bc} \varepsilon_{bc}}{S_{bc0} + S_{SRC}} \right)^2 + \left( \frac{G_{ca} \varepsilon_{ca}}{S_{ca0} + S_{SRC}} \right)^2 \right\} - r_{13}^2 = 0 \quad (12)$$

where  $r_{13}$  is the damage threshold,  $S_{cT}$  is the through the thickness tensile strength for tensile  $\varepsilon_c$ , and  $S_{bc0}$  and  $S_{ca0}$  are the quasi-static shear strengths. The damage surface due to equation (12) is parallel to the composite layering plane. Under compressive through the thickness strain,  $\varepsilon_c < 0$ ,

the damaged surface (delamination) is considered to be “closed”, and the shear strengths are assumed to depend on the compressive normal strain  $\varepsilon_c$  similar to the Mohr-Coulomb theory, i.e.:

$$S_{SRC} = E_c \tan(\varphi) \langle -\varepsilon_c \rangle \quad (13)$$

where  $\varphi$  is the Coulomb’s friction angle. When damage predicted by this criterion occurs within elements that are adjacent to the ply interface, the failure plane is expected to be parallel to the layering planes, and, thus, can be referred to as the delamination mode. Note that a scale factor  $S$  is introduced to provide better correlation of delamination area with experiments. The scale factor  $S$  can be determined by fitting the analytical prediction to experimental data for the delamination area.

**DAMAGE PROGRESSION MODEL**

A set of damage variables  $\varpi_i$  with  $i = 1, \dots, 6$ ; are introduced to relate the onset and growth of damage to stiffness losses in the material. The compliance matrix  $[S]$  is related to the damage variables as (Matzenmiller, et al., 1995):

$$[S] = \begin{bmatrix} \frac{1}{(1-\varpi_1)E_a} & \frac{-\nu_{ac}}{E_a} & \frac{-\nu_{bc}}{E_b} & 0 & 0 & 0 \\ \frac{-\nu_{ac}}{E_a} & \frac{1}{(1-\varpi_2)E_a} & \frac{-\nu_{bc}}{E_b} & 0 & 0 & 0 \\ \frac{-\nu_{bc}}{E_b} & \frac{-\nu_{bc}}{E_b} & \frac{1}{(1-\varpi_3)E_c} & 0 & 0 & 0 \\ 0 & 0 & 0 & \frac{1}{(1-\varpi_4)G_{ab}} & 0 & 0 \\ 0 & 0 & 0 & 0 & \frac{1}{(1-\varpi_5)G_{bc}} & 0 \\ 0 & 0 & 0 & 0 & 0 & \frac{1}{(1-\varpi_6)G_{ca}} \end{bmatrix} \quad (14)$$

The stiffness matrix  $[C]$  is obtained by inverting the compliance matrix, i.e.,  $[C] = [S]^{-1}$ . As suggested in Matzenmiller, et al., (1995), the growth rate of damage variables,  $\varpi_i$ , is governed by the damage rule of the form:

$$\dot{\varpi}_i = \max \{ \dot{\phi}_j q_{ij} \} \quad (15)$$

where the scalar damage functions  $\dot{\phi}_j$  control the amount of growth and the vector-valued matrix  $q_{ij}$  ( $i = 1, \dots, 6, j = 1, \dots, 13$ ) provide the coupling between the individual damage variables ( $i$ ) and the various damage modes ( $j$ ). Note that there are six damage modes ( $j = 1, \dots, 6$ ) for the “unidirectional lamina model” and seven damage modes ( $j = 7, \dots, 13$ ) for the “fabric lamina

model.” The damage criteria  $f_j - r_j^2 = 0$  of Eqs. (1) to (12) provide the damage surfaces in strain space for the unidirectional and fabric lamina models, respectively. Damage growth,  $\dot{\phi}_j > 0$ , will occur when the strain path crosses the updated damage surface  $f_j - r_j^2 = 0$  and the strain increment has a non-zero component in the direction of the normal to the damage surface, i.e.,  $\sum_i \frac{\partial f_j}{\partial \varepsilon_i} \dot{\varepsilon}_i > 0$ . Combined with damage growth functions  $\gamma_j(\varepsilon_i, \varpi_i)$ ;  $\dot{\phi}_j$  is assumed to have the form:

$$\dot{\phi}_j = \sum_i \gamma_j \frac{\partial f_j}{\partial \varepsilon_i} \dot{\varepsilon}_i \quad (\text{no summation over } j) \quad (16)$$

Choosing

$$\gamma_j = \frac{1}{2} (1 - \phi_j) f_j^{\frac{m_j}{2} - 1} \quad (17)$$

and noting that

$$\sum_i \frac{\partial f_j}{\partial \varepsilon_i} \dot{\varepsilon}_i = \dot{f}_j \quad (18)$$

for the quadratic functions given by Eqs. (1) to (6) and Eqs. (8) to (12), lead to:

$$\dot{\phi}_j = \frac{1}{2} (1 - \phi_j) f_j^{\frac{m_j}{2} - 1} \dot{f}_j \quad (19)$$

where  $\phi_j$  is the scalar damage function associated with the  $j^{\text{th}}$  failure mode, and  $m_j$  is a material constant for softening behavior. The scalar damage function  $\phi_j$  can be obtained by integrating Eq. (19) as follows:

$$\begin{aligned} f_j = r_j^2 \quad \rightarrow \quad \dot{f}_j = 2r_j \dot{r}_j \quad \& \quad f_j^{\frac{m_j}{2} - 1} = r_j^{m_j - 2} \\ \dot{\phi}_j = (1 - \phi_j) r_j^{m_j - 1} \dot{r}_j \quad \rightarrow \quad \int_0^{\phi_j} \frac{d\phi_j}{(1 - \phi_j)} = \int_0^{r_j} r_j^{m_j - 1} dr_j \quad \dots \rightarrow \quad \phi_j = 1 - \exp\left(\frac{1}{m_j} (1 - r_j^{m_j})\right) \end{aligned} \quad (20)$$

The damage coupling matrix  $q_{ij}$  is considered for the unidirectional and fabric lamina models as follows.

# DAMAGE COUPLING MATRIX FOR UNIDIRECTIONAL LAMINA MODEL

Eq. (21) is the damage coupling matrix, and Fig. 2 illustrates how Eq. (21) is associated with the modulus reduction for the unidirectional lamina model.

$$q_{ij}^U = \begin{bmatrix} 1 & 1 & 1 & 0 & 0 & 0 \\ 0 & 0 & 1 & 1 & 1 & 0 \\ 0 & 0 & 1 & 1 & 1 & 1 \\ 1 & 1 & 1 & 0 & 0 & 1 \end{bmatrix} \quad i = 1, \dots, 6; j = 1, \dots, 6. \quad (21)$$













UD DAMAGE TYPES		FIBER DAMAGE MODES			MATRIX DAMAGE MODES		
UD DAMAGE MODES		MODE 1u j = 1	MODE 2u j = 2	MODE 3u j = 3	MODE 4u j = 4	MODE 5u j = 5	MODE 6u j = 6
MODULI	$q_{ij}^U$						
$E_a$		1	1	1	0	0	0
$E_b$		0	0	1	1	1	0
$E_c$		0	0	1	0	0	1
$G_{ab}$		1	1	1	1	1	0
$G_{bc}$		0	0	1	1	1	1
$G_{ca}$		1	1	1	0	0	1

Figure 2: Coupling of Different Damage Modes to the Associated Reduction in Moduli for Unidirectional Lamina Model.

# DAMAGE COUPLING MATRIX FOR FABRIC LAMINA MODEL

Eq. (22) is the damage coupling matrix, and Fig. 3 illustrates how Eq. (22) is associated with the modulus reduction for the fabric lamina model.

$$q_{ij}^F = \begin{bmatrix} 1 & 0 & 1 & 0 & 1 & 0 & 0 \\ 0 & 1 & 0 & 1 & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 & 1 & 0 & 1 \\ 1 & 1 & 1 & 1 & 1 & 1 & 0 \\ 0 & 1 & 0 & 1 & 1 & 0 & 1 \\ 1 & 0 & 1 & 0 & 1 & 0 & 1 \end{bmatrix} \quad i = 1, \dots, 6; j = 7, \dots, 13. \quad (22)$$














PW DAMAGE TYPES		FIBER DAMAGE MODES					MATRIX DAMAGE MODES	
PW DAMAGE MODES		MODE 1f j = 7	MODE 2f j = 8	MODE 3f j = 9	MODE 4f j = 10	MODE 5f j = 11	MODE 6f j = 12	MODE 7f j = 13
MO -DU -LI	$q_{ij}^F$							
$E_a$		1	0	1	0	1	0	0
$E_b$		0	1	0	1	1	0	0
$E_c$		0	0	0	0	1	0	1
$G_{ab}$		1	1	1	1	1	1	0
$G_{bc}$		0	1	0	1	1	0	1
$G_{ca}$		1	0	1	0	1	0	1

Figure 3: Coupling of Different Damage Modes to the Associated Reduction in Moduli for Fabric Lamina Model.



Through Eq. (15), the damage coupling matrix  $q_{ij}$  relates the individual damage variables  $\varpi_i$  to the various damage modes provided by the scalar damage functions  $\phi_j$  for the unidirectional and fabric lamina models.

**Unidirectional Fiber Modes 1u, 2u, & 3u:** For the unidirectional lamina model, the damage coupling vectors  $q_{i1}$  and  $q_{i2}$  of equation (21) are chosen such that the fiber tension-shear and compressive damage modes 1u and 2u, Eqs. (1) & (2), provide the reduction of elastic moduli  $E_a$ ,  $G_{ab}$ , and  $G_{ca}$ , due to  $\varpi_1$ ,  $\varpi_4$  and  $\varpi_6$ , respectively. The coupling vector  $q_{i3}$  provides that all the elastic moduli are reduced due to the fiber crush damage mode 3u, Eq. (3).

**Unidirectional Matrix Modes 3u, 4u, & 5u:** For the transverse matrix damage modes 4u and 5u, Eqs. (4) & (5),  $q_{i4}$  and  $q_{i5}$  provide the reduction of  $E_b$ ,  $G_{ab}$  and  $G_{bc}$ , while for the through thickness matrix damage mode 6u,  $q_{i6}$  provides the reduction of  $E_c$ ,  $G_{bc}$ , and  $G_{ca}$ .

**Fabric Fiber Modes 1f, 2f, 3f, 4f, & 5f:** For the fabric lamina model, the damage coupling vectors  $q_{i7}$ ,  $q_{i8}$ ,  $q_{i9}$  and  $q_{i10}$  are chosen for the fiber tension-shear and compressive damage modes 1f to 4f, Eqs. (8), & (9); such that the fiber damage in either the fill or warp direction results in stiffness reduction in the loading direction and in the related shear directions. For the fiber crush damage mode 5f, Eq (10), the damage coupling vector  $q_{i11}$  is chosen such that all the stiffness values are reduced as an element is failed under the crush mode.

**Fabric Matrix Modes 6f, & 7f:** For the in-plane matrix shear failure mode 6f given by Eq. (11), the stiffness reduction due to  $q_{i12}$  is limited to in-plane shear modulus, while the through thickness matrix damage (delamination) mode 7f, the coupling vector  $q_{i13}$  is chosen for the through thickness tensile modulus and transverse shear moduli.

## NON-LINEAR PROGRESSIVE DAMAGE MODEL OF MAT162

Utilizing the damage coupling matrix given by Eqs. (21) & (22), and the scalar damage function given by Eq. (20), the damage variables  $\varpi_i$  can be obtained from Eq. (15) for an individual failure mode j as:

$$\varpi_i = 1 - \exp\left(\frac{1}{m_j}(1 - r_j^{m_j})\right), \rightarrow r_j \geq 1 \quad (23)$$

Note that the damage thresholds  $r_j$  given in the damage criteria of Eqs. (1) to (12) are continuously increasing functions with increasing damage. The damage thresholds have an initial value of one, which results in a zero value for the associated damage variable  $\varpi_i$  from Eq. (23). This provides an initial elastic region bounded by the damage functions in strain space. The nonlinear response is modeled by loading on the damage surfaces to cause damage growth with increasing damage thresholds and the values of damage variables  $\varpi_i$ . After damage initiated, the progressive damage model assumes linear elastic response within the part of strain space bounded by the updated damage thresholds. The elastic response is governed by the reduced stiffness matrix associated with the updated damage variables  $\varpi_i$  given in Eq. (14).

In defining the non-linear stress-strain behavior of a composite material in a specific direction  $k$ , a damage threshold  $r_k$  ( $k = 1, \dots, 6$ ) can also be expressed as the ratio between the current total strain in the  $k^{\text{th}}$  direction and the corresponding yield strain.

$$r_k = \frac{\varepsilon_k}{\varepsilon_{ky}} \quad (24)$$

From Eq. 14, the Young's modulus in the  $k^{\text{th}}$  direction can now be expressed as:

$$E_k = (1 - \varpi_k) E_{k0} = E_{k0} \exp \left( \frac{1}{m_k} \left( 1 - \frac{\varepsilon_k}{\varepsilon_{ky}} \right)^{m_k} \right) \quad (25)$$

Since the reduced modulus is also considered linear, the stress-strain relationship of the damaged material can now be expressed as:


$$\sigma_k = E_k \varepsilon_k = E_{k0} \varepsilon_k \exp \left( \frac{1}{m_k} \left( 1 - \frac{\varepsilon_k}{\varepsilon_{ky}} \right)^{m_k} \right) \quad (26)$$

Recognizing the fact that  $\sigma_{ky} = E_{k0} \varepsilon_{ky}$  Eq. (26) can also be expressed as:

$$\frac{\sigma_k}{\sigma_{ky}} = \frac{\varepsilon_k}{\varepsilon_{ky}} \exp \left( \frac{1}{m_k} \left( 1 - \frac{\varepsilon_k}{\varepsilon_{ky}} \right)^{m_k} \right) \quad (27)$$

Fig. 4 shows the plot of Eq. (27) for different values of damage softening parameter,  $m$ . Note that the value of  $r = \varepsilon / \varepsilon_y \leq 1$ , represent the linear-elastic part of the stress-strain behavior, and Eq. (27) represents the post-yield damage softening behavior for  $r = \varepsilon / \varepsilon_y \geq 1$ .

It is well known that it is difficult to obtain the softening response of most quasi-brittle materials including fiber-reinforced composites. The softening response heavily depends on the set-up and test machines, which can lead to very scattered results. Consequently the choice of damage parameters for each mode becomes an open issue. Generally, smaller values of  $m$  make the material more ductile whereas higher values give the material more brittle behavior. A methodology to systematically determine the model material properties for penetration modeling has been successfully established in [Xiao et al., 2005].

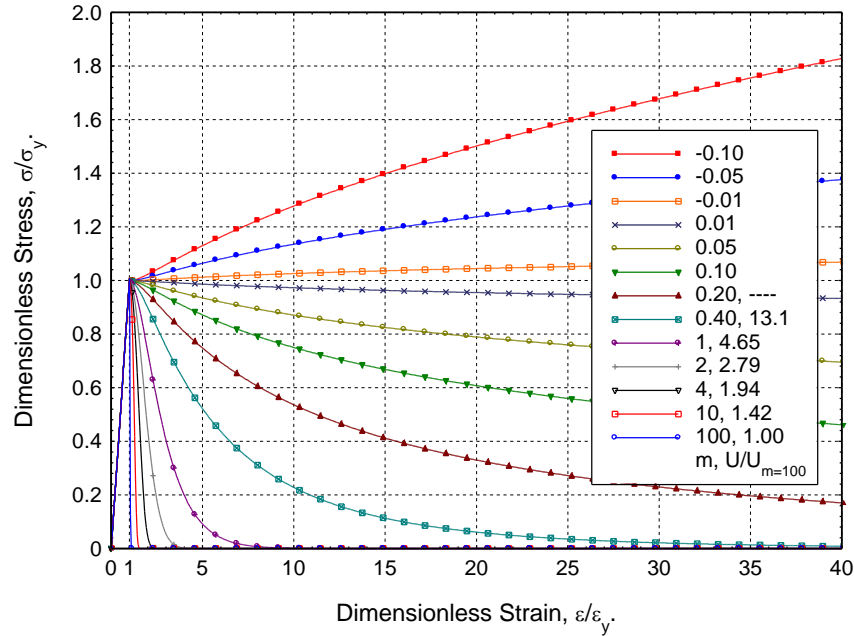

**Figure 4: Non-Linear Progressive Damage Model of MAT162. Post-Yield Damage Softening of a Composite as a Function of Damage Softening Parameter  $m$ .**

In MAT 162, the damage softening parameter  $m_1$  controls the tensile and compressive fiber failure mode in a direction, and  $m_2$  controls the transverse compressive matrix failure mode in b direction for the “unidirectional lamina model.” However, for fabric the “fabric lamina model,”  $m_2$  controls the softening of tensile and compressive fiber failure mode in b direction.  $m_3$  is for softening related to fiber crush mode, and  $m_4$  is for both perpendicular and parallel matrix mode for “unidirectional” case, and for both in-plane matrix failure and through the thickness matrix failure for “fabric” case. Detail analysis on m parameters on the stress-strain behavior can be found in Ref. [Gama et al., 2009].

## ADDITIONAL DISCUSSION ON MODULI AND STRENGTH REDUCTION

When fiber tension-shear damage is predicted in a layer by equation (1) or (8), the load carrying capacity of that layer in the associated direction is reduced to zero according to damage variable Eq. (23). For compressive fiber damage due to equation (2) or (9), the layer is assumed to carry a residual axial load in the damaged direction. The damage variables of Eq. (23) for the compressive modes have been modified to account for the residual strengths of  $S_{aCR} = S_{aC} \times S_{FFC}$  and  $S_{bCR} = S_{bC} \times S_{FFC}$  in the fill and warp directions, respectively.

For through thickness matrix (delamination) failure given by equation (6) or (12), the in-plane load carrying capacity within the element is assumed to be elastic (i.e., no in-plane damage). The load carrying behavior in the through thickness direction is assumed to depend on the opening or closing of the matrix damage surface. For tensile mode,  $\varepsilon_c > 0$ , the through thickness stress components are softened and reduced to zero due to the damage criteria described above.

For compressive mode,  $\varepsilon_c < 0$ , the damage surface is considered to be closed, and thus,  $\varepsilon_c$  is assumed to be elastic, while  $\varepsilon_{bc}$  and  $\varepsilon_{ca}$  are allowed to reduce to sliding friction traction of equation (7) or (13). Accordingly, for the through thickness matrix failure under compressive mode, the damage variable equation is further modified such that the residual sliding strength value is equal to  $S_{SRC}$ .

## EFFECT OF STRAIN RATES ON STRENGTH AND MODULI

The effect of strain-rate on the nonlinear stress-strain response of a composite layer is modeled by a logarithmic strain-rate dependent function for the moduli and strength of the form:

$$\frac{X_{RT}}{X_0} = 1 + C_{rate} \ln \left( \frac{\dot{\varepsilon}}{\dot{\varepsilon}_0} \right) \quad (28)$$

where,  $X_{RT}$  is the rate dependent property of interest at an average strain rate of  $\dot{\varepsilon}$ , and  $X_0$  is the quasi-static property of interest at an average reference strain rate of  $\dot{\varepsilon}_0$ . In the present MAT162 formulation, the reference strain rate is chosen to be:

$$\dot{\varepsilon}_0 = 1 \text{ s}^{-1} \quad (29)$$

**This implies, that the unit of time in LS-DYNA® MAT162 analysis has to be second (s). If millisecond (ms) or microsecond (us) time units are used, the rate effects will not be effective!**

## EFFECT OF STRAIN RATE ON STRENGTH PROPERTIES

One average rate parameter, CERATE1 or  $C_{rate1}$  is used to add rate effects on strength properties as follows:

$$\{S_{RT}\} = \{S_0\} \left( 1 + C_{rate1} \ln \left( \frac{\{\dot{\varepsilon}\}}{\dot{\varepsilon}_0} \right) \right) \quad (30)$$

where, the strength and strain rate matrices are given by Eq. (31). Note that the through thickness tensile strength  $S_{cT}$ , and the shear strengths  $S_{ab}$ ,  $S_{bc}$ , &  $S_{ca}$ ; are not considered as rate dependent in MAT162 formulation.

## EFFECT OF STRAIN RATE ON MODULI

Three rate parameters,  $C_{rate2}$ ,  $C_{rate3}$ , &  $C_{rate4}$  are used to add rate effects on three axial and three shear moduli as presented in Eq. (32), where, the moduli, strain rate, and rate parameter matrices

are given by Eq. (33). Note that the rate effects on both the axial moduli,  $E_a$  &  $E_b$ , are controlled by the rate parameter  $C_{rate2}$ , and that for the through thickness modulus,  $E_c$ , by  $C_{rate4}$ . In addition, the rate effects on the shear moduli,  $G_{ab}$ ,  $G_{bc}$ , &  $G_{ca}$ , are controlled by the rate parameter  $C_{rate3}$ .

$$\{S\} = \begin{Bmatrix} S_{aT} \\ S_{aC} \\ S_{bT} \\ S_{bC} \\ S_{FC} \\ S_{FS} \end{Bmatrix}, \quad \{\dot{\epsilon}\} = \begin{Bmatrix} |\dot{\epsilon}_a| \\ |\dot{\epsilon}_b| \\ |\dot{\epsilon}_b| \\ |\dot{\epsilon}_c| \\ (\dot{\epsilon}_{ca}^2 + \dot{\epsilon}_{bc}^2)^{1/2} \end{Bmatrix}, \quad (31)$$

$$\{E_{RT}\} = \begin{Bmatrix} E_a \\ E_b \\ E_c \\ G_{ab} \\ G_{bc} \\ G_{ca} \end{Bmatrix}, \quad \{\dot{\epsilon}\} = \begin{Bmatrix} |\dot{\epsilon}_a| \\ |\dot{\epsilon}_b| \\ |\dot{\epsilon}_c| \\ |\dot{\epsilon}_{ab}| \\ |\dot{\epsilon}_{bc}| \\ |\dot{\epsilon}_{ca}| \end{Bmatrix}, \quad \{C_{rate}\} = \begin{Bmatrix} C_{rate2} \\ C_{rate2} \\ C_{rate4} \\ C_{rate3} \\ C_{rate3} \\ C_{rate3} \end{Bmatrix} \quad (32)$$

$$(33)$$

A discussion of rate dependent MAT162 properties can be found in Ref. [Gama & Gillespie Jr. 2011].

## ELEMENT EROSION

A failed element is eroded in any of three different ways:

1. If fiber tensile failure in a “unidirectional” layer is predicted in the element and the axial tensile strain is greater than E\_LIMIT. For a “fabric” layer, both in-plane directions are failed and exceed E\_LIMIT.
2. If compressive relative volume (ratio of current volume to initial volume) in a failed element is smaller than ECRSH.
3. If expansive relative volume in a failed element is greater than EEXPEN.

**FINITE ELEMENT MODELING TIPS**

- One point integration solid element (TYPE = 1) can be used for MAT162.
- In order to observe the delamination at the interface between two adjacent laminas, two different PART IDs with different MAT IDs for each parts and with different material orientation angles (BETA in the MAT162 cards) must be defined at the interface of interest. If it is required to model the delamination at the interface between two plies with the same material orientation angles, those two angles must be defined in different ways in each PART, e.g., BETA = 0.00 & BETA = 180.00.
- \*DATABASE\_EXTENT\_BINARY must be included to check history variables.
- Type of \*HOURGLASS need to be checked for minimum hourglass energy over the duration of the LS-DYNA solution.

**DAMAGE HISTORY PARAMETERS**

Information about the damage history variables for the associated failure modes can be plotted in LS-POST. These additional variables are tabulated below:

History Variable			Description	Value	LS-POST Components
#	Uni	Fabric			
1	$\max(r_1, r_2)$	$\text{Max}(r_7, r_9)$	Fiber mode in a	0 - elastic > 1- damage thresholds, Eqs. (1-6) to (8-12)	7
2	-	$\text{Max}(r_8, r_{10})$	Fiber mode in b		8
3	$r_3$	$r_{11}$	Fiber crush mode		9
4	$r_5$	$r_{12}$	Perpendicular matrix mode		10
5	$r_6$	$r_{13}$	Parallel matrix/ delamination mode		11
6			Element delamination indicator	0 – no delamination 1 – with delamination	12

**REFERENCES**







- Yen, C.F., (2002), “Ballistic Impact Modeling of Composite Materials,” Proceedings of 7<sup>th</sup> International LS-DYNA Users Conference, May, 2002, Dearborn, Michigan, pp.6.15-6.26.
- Matzenmiller, A., Lubliner, J., and Taylor, R.L. (1995). “A Constitutive Model for Anisotropic Damage in Fiber-Composites,” *Mechanics of Materials*, 20, pp. 125-152.
- Xiao, J. R., Gama, B. A., and Gillespie Jr., J. W., “Progressive Damage and Delamination in Plain Weave S-2 Glass/SC-15 Composites under Quasi-Static Punch Shear Loading,” *Composite Structures*, 2007, Vol. 78, pp. 182-196.
- Gama, B. A., Travis A. Bogetti, and Gillespie, J. W. (1009). “Progressive Damage Modeling of Plain-Weave Composites using LS-Dyna Composite Damage Model MAT162,” Proceedings and CD Rom of 7th European LS-DYNA Conference, May 14-15, Salzburg, Austria, 2009.
- Gama, B. A., and Gillespie, J. W. (2011). “Finite Element Modeling of Impact, Damage and Penetration of Thick-Section Composites,” *International Journal of Impact Engineering*, Vol. 38, pp. 181-197.
- Bazle Z. (Gama) Haque, Jessica L. Harrington, Ishita Biswas, and John W. Gillespie Jr. “Perforation and Penetration of Composites.” CD Proceedings, SAMPE 2012 Baltimore, MD. May 21-24, 2012.
- Bazle Z. (Gama) Haque, Jessica L. Harrington, and John W. Gillespie Jr. “Multi-hit ballistic impact on S-2 glass/SC15 thick-section composites: Finite element analyses.” *Journal of Strain Analysis*, Vol. 47, No. 7, 2012. DOI: 10.1177/0309324712456823.
- Bazle Z. (Gama) Haque, Richard J. Stanton, and John W. Gillespie Jr. “Perforation Mechanics of Thin Composites.” CD Proceedings, SAMPE 2013 Long Beach, CA. May 6-9, 2013.
- Jordan, J. B., Naito, C. J., and (Gama) Haque, B. Z. Progressive damage modeling of plain weave E-glass/phenolic composites. *Composites B*, Vol. 61, May 2014, pp. 315-323.

## APPENDIX A: MAT162 PROPERTIES AND PARAMETERS

### MAT162 ELASTIC AND STRENGTH PROPERTIES










In addition to ASTM standard test methods, UD-CCM has developed non-standard experimental techniques and computational methodologies to determine all material properties and parameters needed for MAT162.

#### MAT162 ELASTIC & STRENGTH PROPERTIES: ASTM STANDARD TESTS

Properties, Parameters	Test Method	Specimen	Dimensions (mm)	Miscellaneous
$E_1, \nu_{12}, X_1^T$	0° Tension (ASTM D3039)		254×25.4×1	
$E_2, \nu_{21}, X_2^T$	90° Tension (ASTM D3039)		175×25.4×2	
$X_1^C$	0° Compression (ASTM D3410)		155×25.4×2	
$X_2^C$	90° Compression (ASTM D3410)		155×25.4×2	
$E_3, \nu_{31}, \nu_{32}, X_3^T$	Thru-thickness Tension/Compression (no standard)		20×20×20 15×15×30	
$G_{12}, G_{23}, G_{31}$ $S_{12}, S_{23}, S_{31}$	In-Plane +/-45 Tension, Rail-Shear & V-Notch Shear (ASTM D5379)		76×4.5×20	Shear in 1-2, 2-3, 3-1 planes



## MAT162 PROPERTIES & PARAMETERS: NON-STANDARD UD-CCM TEST & COMPUTATIONAL METHODOLOGIES

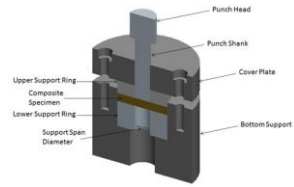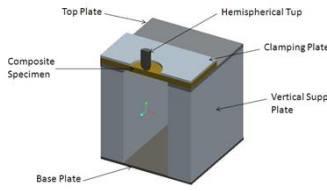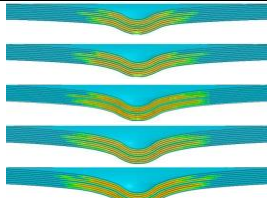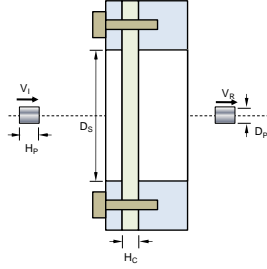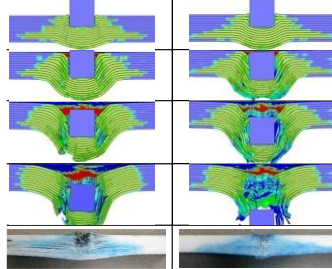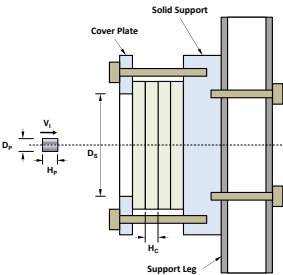$E_3, PHIC$	Out-of-Plane Off-Axis Compression (no standard)		15x15x15	$\theta = 0^\circ, 15^\circ, 30^\circ, 45^\circ, 60^\circ, 75^\circ$
$SFFC$	Open Hole Compact Compression Test (no standard)		25x25x13 D = 8~12	Loading along fiber direction for both UD and PW Composites
$SFC, SFS$	Quasi-Static Punch Shear Test (QS-PST) Punch Crush Strength (PCS) & Punch Shear Strength (PSS) (BZH Methodology)		25 mm Discs 100x100 Plates 150x150 Plates	SPR = $D_s/D_p$ SPR = 0 for SFC SPR = 1.1 for SFS
$OMGMX$ & Damage Softening Parameters $m_1$ to $m_4$	Low Velocity Impact Experiments; & Numerical Simulation (BZH Methodology)		100x150 Plates	 Energy Levels: 30J to 70J @ an increment of 10J
Erosion Parameters $E_{LIMIT}$ $E_{EXP}$ Rate Parameters $C_{rate1}$ to $C_{rate4}$	Hopkinson Bar Testing Dynamic Punch Shear Ballistic Testing  Numerical Simulation of Ballistic Tests (BZH Methodology)		150x150x15 Plates	
Crush Parameters, $SFC, ECRSH$	Depth of Penetration Impact Experiments; & Numerical Simulation (BZH Methodology)		305x205x50 Plates	 Impact at 300 to 800 m/s @ an interval of 50 m/s. Measure DoP as a function of impact velocity. Parametrically determine SFC & ECRSH to match the Experimental Data.

## MAT162 DATABASE OF COMPOSITE PROPERTIES

Properties, Unit	UD S-2 Glass/SC15	PW S-2 Glass/SC15	PW S- Glass/Phenolic OWENS Corning	PW E- Glass/Phenolic U.S. AERDC
$V_f$	0.60	0.53	0.62	0.66
$\rho_c$ , g/cm <sup>3</sup>	1.85	1.85	2.00	2.107
E1, GPa	64.0	27.5	38.6	29.15
E2, GPa	11.8	27.5	31.9	29.15
E3, GPa	11.8	11.8	12.0	11.00
$\nu_{21}$	0.0535	0.110	0.100	0.078
$\nu_{31}$	0.0535	0.180	0.200	0.109
$\nu_{32}$	0.449	0.180	0.200	0.109
G12, GPa	4.30	2.90	4.50	1.54
G23, GPa	3.70	2.14	2.90	1.67
G31, GPa	4.30	2.14	3.10	1.67
X1T, MPa	1380	604	402	531
X1C, MPa	770	291	138	131
X2T, MPa	47	604	592	531
X2C, MPa	137	291	204	131
X3T, MPa	47	58	52	50
SFC, MPa	850	850	1540	870
SFS, Mpa	250	300	172	160
S12, MPa	76	75	73	35
S23, MPa	38	58	49	27
S31, MPa	76	58	49	27
AM1	100.00	2.00	1.00	1.00
AM2	10.00	2.00	1.00	1.00
AM3	1.00	0.50	0.50	0.50
AM4	0.10	0.20	-0.20	0.20/-0.20
PHIC	10	10	10	10
SFFC	0.10	0.30	0.30	0.30
Crate1	0.00	0.03	0.03	0.03
Crate2	0.00	0.00	0.00	0.00
Crate3	0.00	0.03	0.03	0.03
Crate4	0.00	0.03	0.03	0.03
SDELM	1.2	1.2	1.2	1.2
OMGMX	0.999	0.999	0.998 (LVI) 0.997 (DoP)	0.994
E_LIMT	4.5	4.5	5.0	4.0
EEXPN	4.5	4.5	5.0	4.0
ECRSH	0.001	0.001	0.700	0.500
AMODEL	1 (UD)	2 (PW)	2 (PW)	2 (PW)
SOURCE	Ref. [A]	Ref. [B]	Ref. [C]	Ref. [D]

### REFERENCES

- [A]. Kang, S-K, Gama, B. A., and Gillespie, Jr., J. W. SAMPE 2010.  
 [B]. Gama, B. A., and Gillespie, Jr., J. W. 11th European LS-Dyna Conference, 2009.  
 [C]. (Gama) Haque, B. Z., Hartman, D. R., et al. SAMPE 2011, ASC 2012.  
 [D]. Jordan, J., & (Gama) Haque, B. Z., et al. Technical Report, 2012.

## APPENDIX B: GENERAL DISCUSSION

### DISCUSSION ON REFERENCE STRAIN RATE

The reference strain rate in MAT162 is set to 1. If the time unit in LS-DYNA computation is set to seconds (s), then this reference strain rate is  $\dot{\epsilon}_0 = 1s^{-1}$ . This raises a question of how to calculate the rate parameters,  $C_{rate}$ , for different time units of LS-DYNA computations.

Consider a fictitious experimental set of strength data as a function of strain rates measured in  $s^{-1}$ . Table SR-1 shows this set of data. Fig. SR-1a shows the plot of this set of experimental data. The MAT162 rate equation is expressed as:

$$\frac{X_{RT}}{X_0} = 1 + C_{rate} \ln \left( \frac{\dot{\epsilon}}{\dot{\epsilon}_0} \right) \quad (SR-1)$$

Table SR-1: A Fictitious Experimental Set of Strength Data and Dimensionless Data for Reference Strain Rate,  $\dot{\epsilon}_0 = 1.0 \times 10^{-6} s^{-1}$ .

Strain Rate, $s^{-1}$	Strength, MPa	$\dot{\epsilon}_0 = 1.0 \times 10^{-6} s^{-1}$	$X_0 = 600 MPa$
$\dot{\epsilon}$	$X_{RT}$	$\dot{\epsilon}/\dot{\epsilon}_0$	$X_{RT}/X_0$
1.00E-06	600	1.00E+00	1.0000
1.00E-05	630	1.00E+01	1.0500
1.00E-04	655	1.00E+02	1.0917
1.00E-03	680	1.00E+03	1.1333
1.00E-02	710	1.00E+04	1.1833
1.00E-01	740	1.00E+05	1.2333
1.00E+00	765	1.00E+06	1.2750
1.00E+01	790	1.00E+07	1.3167
1.00E+02	820	1.00E+08	1.3667
1.00E+03	850	1.00E+09	1.4167
1.00E+04	875	1.00E+10	1.4583

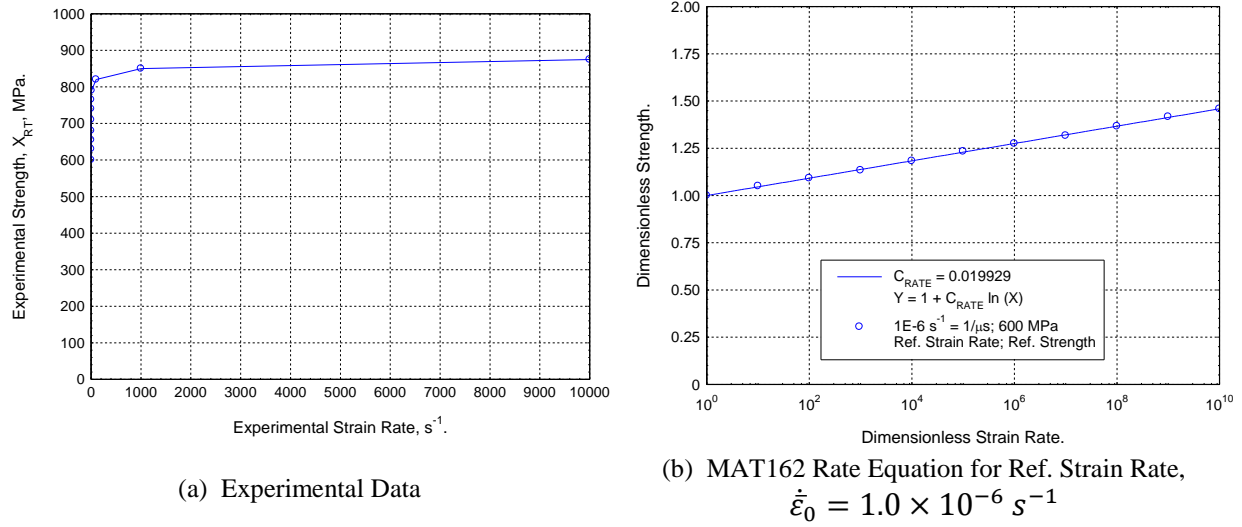


Figure SR-1: A Fictitious Experimental Set of Strength MAT162 Rate Equation for Reference Strain Rate,  $\dot{\epsilon}_0 = 1.0 \times 10^{-6} s^{-1}$ .

We will use the Table SR-1 data to determine the rate parameter for different time units in LS-DYNA computations.

### 1. Reference Strain Rate $\dot{\epsilon}_0 = 1.0 \times 10^{-6} s^{-1} = 1/\mu s$ for LS-DYNA Time Unit of Micro-Second

Consider the LS-DYNA time unit be micro-second. Also consider the reference strain rate in micro-second time unit to be  $\dot{\epsilon}_0 = 1 \mu s^{-1} = 1.0 \times 10^{-6} s^{-1}$ . From Table SR-1, the reference strength is  $X_0 = 600 MPa$ . We can then normalize the experimental data with the reference strain rate and reference strength and the dimensionless values ( $\dot{\epsilon}/\dot{\epsilon}_0$ ,  $X_{RT}/X_0$ ) are also presented in Table SR-1. The dimensionless strength and strain rates can then be plotted and is presented in Fig. SR-1b. Eq. (SR-1) can then be used to fit the dimensionless experimental data in determining the rate parameter,  $C_{rate}$ , and for the fictitious experimental data presented in Table SR-1 is found to be,  $[C_{rate}]_{\dot{\epsilon}_0=1 \mu s^{-1}} = 0.019929$ .

### 2. Reference Strain Rate $\dot{\epsilon}_0 = 1.0 \times 10^{-3} s^{-1} = 1/ms$ for LS-DYNA Time Unit of Milli-Second


Consider the LS-DYNA time unit be milli-second. Also consider the reference strain rate in milli-second time unit to be  $\dot{\epsilon}_0 = 1 ms^{-1} = 1.0 \times 10^{-3} s^{-1}$ . The corresponding reference strength is  $X_0 = 680 MPa$ . Table SR-2 shows the dimensionless strain rate and stress data and is plotted in Fig. SR-2a. Note that strain rates  $< 1.0 \times 10^{-3} s^{-1}$  are not considered. This data is curve fitted to determine the rate parameter and is found to be,  $[C_{rate}]_{\dot{\epsilon}_0=1 ms^{-1}} = 0.017812$ .

Table SR-2: A Fictitious Experimental Set of Strength Data and Dimensionless Data for Reference Strain Rate,  $\dot{\epsilon}_0 = 1.0 \times 10^{-3} \text{ s}^{-1}$ , and  $\dot{\epsilon}_0 = 1.0 \text{ s}^{-1}$ .


Strain Rate, $\text{s}^{-1}$	Strength, MPa	$\dot{\epsilon}_0 = 1.0 \times 10^{-3} \text{ s}^{-1}$	$X_0 = 680 \text{ MPa}$	$\dot{\epsilon}_0 = 1.0 \text{ s}^{-1}$	$X_0 = 765 \text{ MPa}$
$\dot{\epsilon}$	$X_{RT}$	$\dot{\epsilon}/\dot{\epsilon}_0$	$X_{RT}/X_0$	$\dot{\epsilon}/\dot{\epsilon}_0$	$X_{RT}/X_0$
1.00E-06	600	-	-	-	-
1.00E-05	630	-	-	-	-
1.00E-04	655	-	-	-	-
1.00E-03	680	1.00E+00	1.0000	-	-
1.00E-02	710	1.00E+01	1.0441	-	-
1.00E-01	740	1.00E+02	1.0882	-	-
1.00E+00	765	1.00E+03	1.1250	1.00E+00	1.0000
1.00E+01	790	1.00E+04	1.1618	1.00E+01	1.0327
1.00E+02	820	1.00E+05	1.2059	1.00E+02	1.0719
1.00E+03	850	1.00E+06	1.2500	1.00E+03	1.1111
1.00E+04	875	1.00E+07	1.2868	1.00E+04	1.1438

### 3. Reference Strain Rate $\dot{\epsilon}_0 = 1.0 \text{ s}^{-1} = 1/\text{s}$ for LS-DYNA Time Unit of Second

Consider the LS-DYNA time unit be second. Also consider the reference strain rate in second time unit to be  $\dot{\epsilon}_0 = 1 \text{ s}^{-1}$ . The corresponding reference strength is  $X_0 = 765 \text{ MPa}$ . Table SR-2 shows the dimensionless strain rate and stress data and is plotted in Fig. SR-2b. Note that strain rates  $< 1.0 \text{ s}^{-1}$  are not considered. This data is curve fitted to determine the rate parameter and is found to be,  $[C_{\text{rate}}]_{\dot{\epsilon}_0=1 \text{ ms}^{-1}} = 0.015600$ .

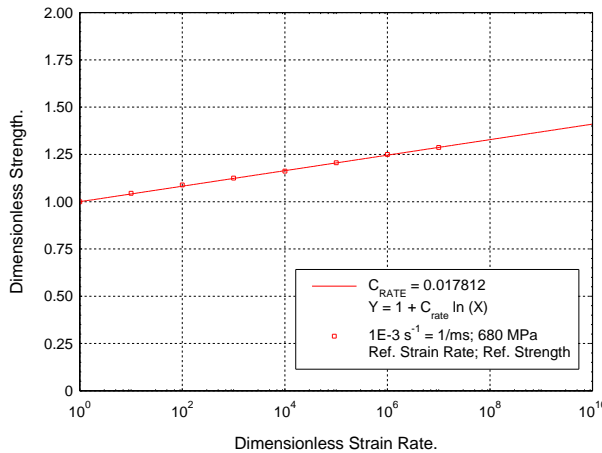

(a) MAT162 Rate Equation for Ref. Strain Rate,  $\dot{\epsilon}_0 = 1.0 \times 10^{-3} \text{ s}^{-1}$

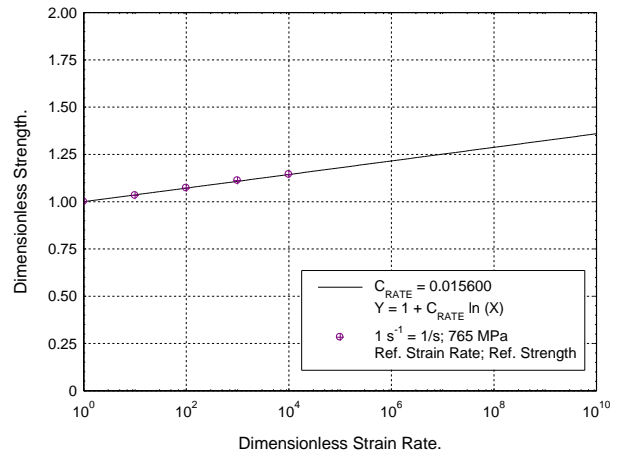

(b) MAT162 Rate Equation for Ref. Strain Rate,  $\dot{\epsilon}_0 = 1.0 \text{ s}^{-1}$

Figure SR-2: MAT162 Rate Equations for Reference Strain Rates,  $\dot{\epsilon}_0 = 1.0 \times 10^{-3} \text{ s}^{-1}$ , and  $\dot{\epsilon}_0 = 1.0 \text{ s}^{-1}$ .

## DISCUSSION ON LAMIANTE ARCHITECTURE AND PREDEFINED DELAMINATION PLANES

A composite laminate may contain several numbers of laminas or plies stacked through-the-thickness of the laminate. If the individual laminas are very thin, it is suggested to combine several laminas into one sub-laminate. Figure LA-1 shows the finite element model of such a sub-laminate with three (3) through-thickness elements.

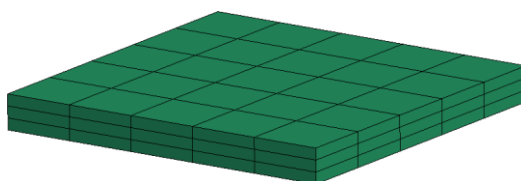


Figure LA-1: Finite Element Model of a Sub-Laminate with Three (3) Through-Thickness Elements.

Once a sub-laminate model is created, one should assign a Part ID to the sub-laminate and associate the **PID** with a Material ID with a pre-defined material angle (**BETA**), e.g.; **PID=1**, **MID=100**, **BETA=0** in Fig. LA-2. Several sub-laminates can be stacked through-the-thickness to build a laminate. Figure LA-2 shows a composite laminate with four (4) sub-laminates stacked through-the-thickness with the stacking sequence [0/90/0/90] and each sub-laminates are assigned with different Part IDs, i.e., **PID=1**, **2**, **3**, **4**. However, since the stacking sequence is taken as [0/90/0/90], only two Material IDs (i.e., **MID=100**, **200**) are sufficient. Note that all duplicate nodes between the PIDs 1 to 4 needs to be merged and the unreferenced nodes be deleted.

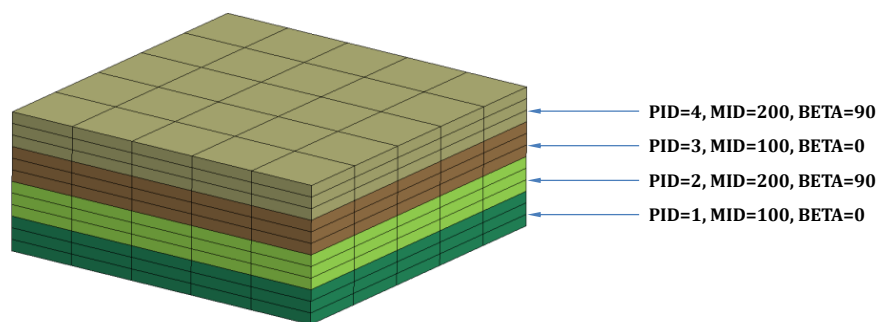


Figure LA-2: Node Merged Finite Element Model of a Laminate consisting of Four (4) Sub-Laminates with the Stacking Sequence [0/90/0/90]. Three Delamination Planes are thus Predefined between PIDs 1&2, 2&3, and 3&4.

According to MAT162 formulations, three pre-defined delamination planes will be automatically defined at the interface between four parts with different material angles (**BETA**). Once delamination between two parts with different material angles is predicted, shear properties of

the elements adjacent to the delamination interface will be degraded to mimic delamination without creating physical surfaces between sub-laminates or parts. The advantage of MAT162 delamination criterion is that it is simple, however, the disadvantage is that the predicted delamination is assigned a thickness equal to one element near the delamination interface and is not physical in nature. This is why, three elements through-the-thickness of a sub-laminate or part is proposed so that the pseudo-delamination is limited to one-third of the thickness of a sub-laminate or part.

Figures LA-3 to 5 show three additional laminate stacking sequences defined with four sub-laminates.

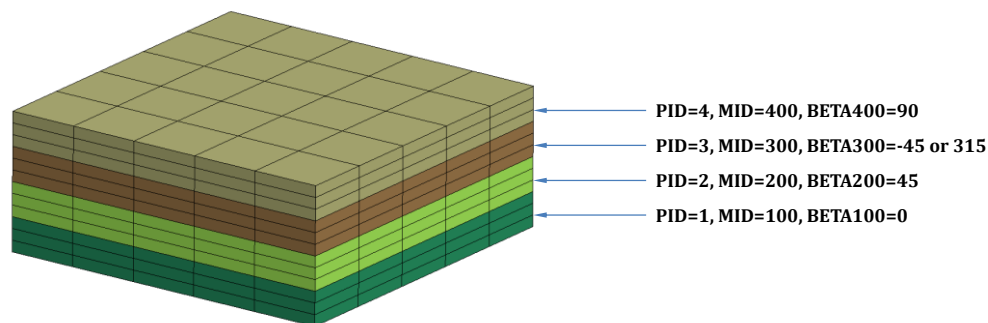


Figure LA-3: Node Merged Finite Element Model of a Laminate consisting of Four (4) Sub-Laminates with the Stacking Sequence [0/45/-45/90]. Three Delamination Planes are thus Predefined between PIDs 1&2, 2&3, and 3&4.

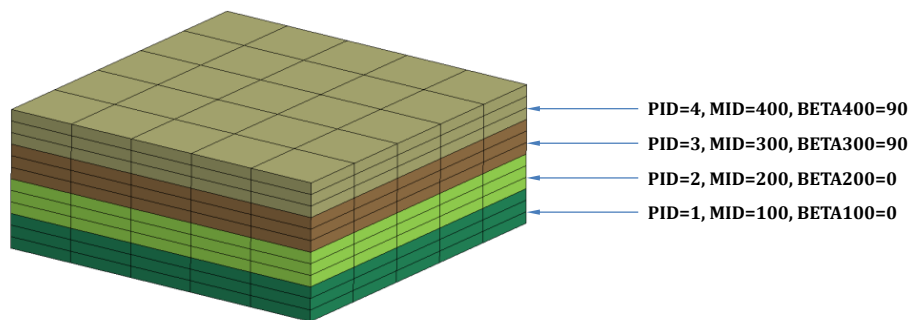


Figure LA-4: Node Merged Finite Element Model of a Laminate consisting of Four (4) Sub-Laminates with the Stacking Sequence [0/0/90/90]. One Delamination Plane is thus Predefined between PIDs 2&3.

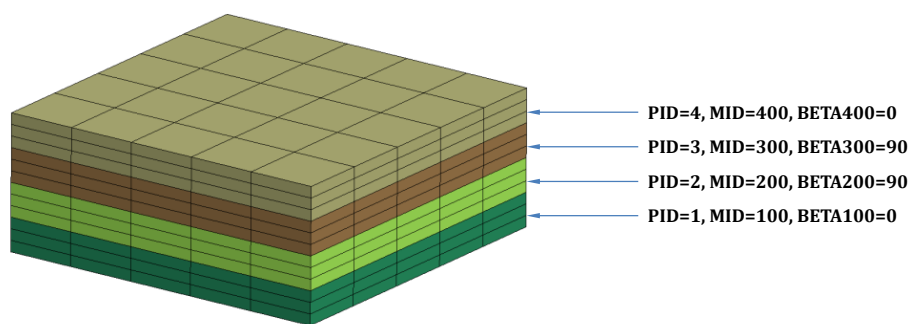


Figure LA-5: Node Merged Finite Element Model of a Laminate consisting of Four (4) Sub-Laminates with the Stacking Sequence [0/90/90/0]. Two Delamination Planes are thus Predefined between PIDs 1&2, and 3&4.

## DISCUSSION ON CONTROL ACCURACY

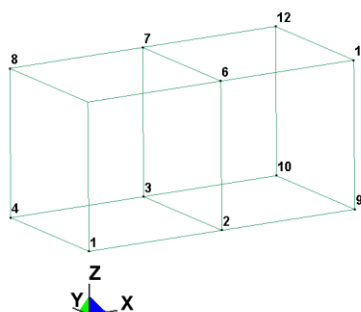


Figure CA-1: Definition of Two Single Elements in the Discussion of Control Accuracy.

In Fig. CA-1, if we choose **AOPT=0** for a composite element and define the element (**EID=1**) with the following node sequence, then the vector **V12** connecting nodes 1 & 2 defines the material direction 1 or A. The vector **V14** connecting nodes 1 & 4 together with the vector **V12** defines the material plane 1-2 or A-B, and the vector cross product  $\mathbf{V12} \times \mathbf{V14}$  defines the through-thickness material direction 3 or C.

```

$-----+-----+-----+-----+-----+-----+-----+-----+
*ELEMENT_SOLID
$-----+-----+-----+-----+-----+-----+-----+-----+
$#   eid      pid      n1      n2      n3      n4      n5      n6      n7      n8
$-----+-----+-----+-----+-----+-----+-----+-----+
      1       100       1       2       3       4       5       6       7       8
$-----+-----+-----+-----+-----+-----+-----+-----+

```

Following the same procedure, one can define the second element (**EID=2**) as follows to be consistent with **AOPT=0**.



```

$-----+-----+-----+-----+-----+-----+-----+-----+-----+
*ELEMENT_SOLID
$-----+-----+-----+-----+-----+-----+-----+-----+-----+
$#   eid      pid      n1      n2      n3      n4      n5      n6      n7      n8
$-----+-----+-----+-----+-----+-----+-----+-----+-----+
      2      100      9      10      3      2      11      12      7      6
$-----+-----+-----+-----+-----+-----+-----+-----+-----+

```

However, if the second element (**EID=2**) is defined as follows, then it is not consistent with **AOPT=0**.


```

$-----+-----+-----+-----+-----+-----+-----+-----+-----+
*ELEMENT_SOLID
$-----+-----+-----+-----+-----+-----+-----+-----+-----+
$#   eid      pid      n1      n2      n3      n4      n5      n6      n7      n8
$-----+-----+-----+-----+-----+-----+-----+-----+-----+
      1      100      1      2      3      4      5      6      7      8
      2      100      2      9      10     3      6      11     12     7
$-----+-----+-----+-----+-----+-----+-----+-----+-----+


```

One can try to fix this problem by choosing **AOPT=2** by defining two vectors **A** (1, 0, 0) & **B** (0, 1, 0) to represent material direction 1 or A and the plane 1-2 or A-B, but this will not correct the problem, instead produce a wrong material response.

Figure CA-2a shows the wrong stress-time plot using **AOPT=2** with the wrong element definition for **EID=2**. In order to solve this problem, the LS-DYNA control card **\*CONTROL\_ACCURACY** can be used which allows **INVARIANT NODE NUMBERING** if the parameter **INN=3** is chosen for solid elements. Figure CA-2b shows the correct stress-time response with **INN=3** in the control accuracy card.

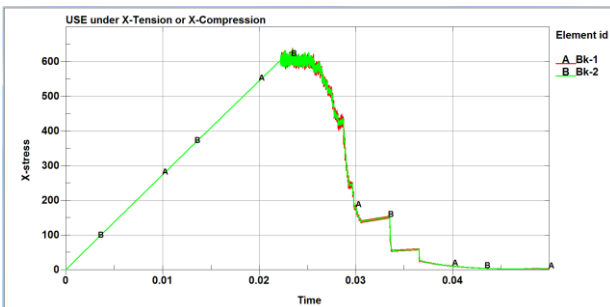

(a) AOPT=2 with INN=1

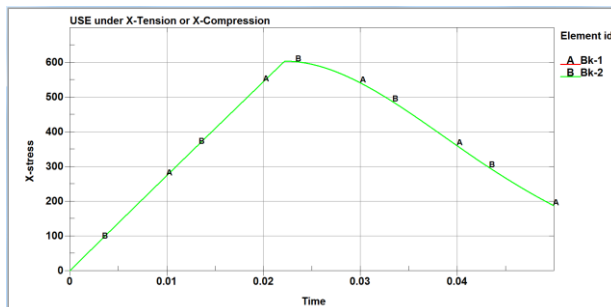

(a) AOPT=2 with INN=3

Figure CA-2: Definition of Two Single Elements in the Discussion of Control Accuracy.

EXAMPLE OF \*CONTROL\_ACCURACY CARD WITH PARAMETERS

```
$-----+-----+-----+-----+-----+-----+-----+
*PARAMETER_EXPRESSION
$-----+-----+-----+-----+-----+-----+-----+
$ PRMR1  EXPRESSION1
$-----+-----+-----+-----+-----+-----+-----+
I INN    3
$-----+-----+-----+-----+-----+-----+-----+
...
...
...
...
...
$-----+-----+-----+-----+-----+-----+-----+
*CONTROL_ACCURACY
$-----+-----+-----+-----+-----+-----+-----+
$#      osu      inn  pidosu
        0      &INN
$-----+-----+-----+-----+-----+-----+-----+
```

AXIS OPTION AOPT AND SWITCHING MATERIAL AXES


Axis options, **AOPT=0 , 2 , 4** has been tested and are found to be working with MAT162 along with the material axes switch options **MACF** without any problems. At present, we are looking at the applicability of axis option **AOPT=1**, and will report when our test is complete.

## APPENDIX C: MAT162 EXAMPLES

### EXAMPLE 1: SPHERE IMPACT ON COMPOSITES An Example of MAT162 Progressive Composite Damage Model

#### A SIMPLE FEA MODEL OF A FOUR LAYER COMPOSITE LAMINATE WITH ONE DELAMINATION PLANE

The FEA model has two parts, each part defining two layers/laminas of a four layers composite laminate. The two bottom layers/laminas with PART ID = 101 is assigned a material angle of zero degree by defining the parameter BETA101 = 0.00 and the same for the top part with PART ID = 102 with the parameter BETA102 = 90.00. A delamination plane is thus defined between two different PART IDs each having a different material angle defined by BETA. For example, if the parameter BETA102 is changed to zero degree, there will be no delamination plane defined in the model.

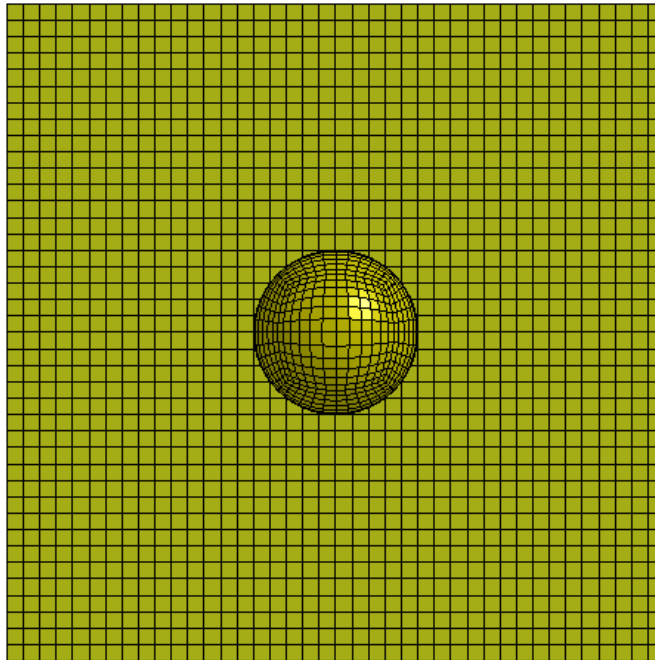

The input files used in this example are summarized below.

**FILE: 001-Sphere-Impact-on-Composite-Plate.key**

```
$-----+-----+-----+-----+-----+-----+-----+-----+
$ Copyright 2015 (C) University of Delaware Center for Composite Materials
$-----+-----+-----+-----+-----+-----+-----+-----+
$ Unit System: mm-tonne-s (millimeter-tonne-second-Newton-MegaPascal)
$-----+-----+-----+-----+-----+-----+-----+-----+
$ Date: April 15, 2015
$ Dr. Bazle Z. (Gama) Haque
$ Senior Scientist of Center for Composite Materials (UD-CCM)
$ Assistant Professor of Mechanical Engineering
$ University of Delaware
$ Newark, DE 19716, USA
$ Tel: (302) 690-4741; E-mail: gama@udel.edu
$-----+-----+-----+-----+-----+-----+-----+-----+
$ Visualizing Damage Modes in LS-PrePost
$ Page-1 Tab-Range: User Min=0 Max=1
$ Toggle Switch: Lcon-ON
$ Page-1 Tab-Fcomp: Misc history var#7 (Fiber Tension-Shear Along A)
$ Page-1 Tab-Fcomp: Misc history var#8 (Fiber Tension-Shear Along B)
$ Page-1 Tab-Fcomp: Misc history var#9 (Fiber Crush)
$ Page-1 Tab-Fcomp: Misc history var#10 (In-Plane Matrix Crack)
$ Page-1 Tab-Fcomp: Misc history var#11 (Transverse Matrix Crack)
$ Page-1 Tab-Fcomp: Misc history var#12 (Delamination between 0 & 90 plies)
$ Delamination between 0 & 90 plies for this specific problem
$-----+-----+-----+-----+-----+-----+-----+-----+
$# Change the NCPU below to match your desired number of CPUs.
$-----+-----+-----+-----+-----+-----+-----+-----+
*KEYWORD MEMORY=10M NCPU=16
$-----+-----+-----+-----+-----+-----+-----+-----+
*PARAMETER_EXPRESSION
$-----+-----+-----+-----+-----+-----+-----+-----+
R us 1.00E-6
R ENDTIME 600.00*us
R NOD3 30.0
R DTBIN 0.01*us
R DTD3 ENDTIME/NOD3
R TSSFAC 0.950
$-----+-----+-----+-----+-----+-----+-----+-----+
I BSORT 1
I DEPTH 5
R PARMAX 1.0025
I SBOPT 5
R SLSFAC 0.010
R SLDTHK 0.001
I NEIPH 36
$-----+-----+-----+-----+-----+-----+-----+-----+
R mps 1000.00
R VX +0.001*mps
R VY +0.001*mps
R VZ -100.00*mps
$-----+-----+-----+-----+-----+-----+-----+-----+
R mm 1.000
R dx 0.01*mm
R dy 0.01*mm
R dz 12.10*mm
$-----+-----+-----+-----+-----+-----+-----+-----+
$ *** MAT162 PROPERTIES & PARAMETERS ***
$-----+-----+-----+-----+-----+-----+-----+-----+
R gmpcc 1.0E-9
R MPa 1.000
R GPa 1.0E+3
$-----+-----+-----+-----+-----+-----+-----+-----+
I MIDP 700
R ROP 7.85*gmpcc
R EP 210.00*GPa
R PRP 0.290
$-----+-----+-----+-----+-----+-----+-----+-----+
I MID101 101
I MID102 102
R BETA101 0.00
```

```
R BETA102 90.00
$-----+-----+-----+-----+-----+-----+
R DENSITY 1.850*gm/cc
R E11      27.5*GPa
R E22      27.5*GPa
R E33      11.8*GPa
$-----+-----+-----+-----+-----+
R NU21     0.110
R NU31     0.180
R NU32     0.180
$-----+-----+-----+-----+-----+
R G12      2.90*GPa
R G23      2.14*GPa
R G31      2.14*GPa
$-----+-----+-----+-----+-----+
R X1T      604.0*MPa
R X1C      291.0*MPa
R X2T      604.0*MPa
R X2C      291.0*MPa
R X3T      58.0*MPa
$-----+-----+-----+-----+-----+
R SFC      850.0*MPa
R SFS      300.0*MPa
$-----+-----+-----+-----+-----+
R S12      75.0*MPa
R S23      58.0*MPa
R S31      58.0*MPa
$-----+-----+-----+-----+-----+
R SFFC     0.300
R PHIC     10.00
R SDELAM   1.200
$-----+-----+-----+-----+-----+
R OMGX     0.999
R ECRSH    0.001
R ELIMIT   4.000
R EEXPX    4.000
$-----+-----+-----+-----+-----+
R AM1FD1   2.00
R AM2FD2   2.00
R AM3FCPS  0.50
R AM4MCDE  0.20
$-----+-----+-----+-----+-----+
R CR1SIG   0.030
R CR2E1E2  0.000
R CR3G     0.030
R CR4E3    0.030
$-----+-----+-----+-----+-----+
*MAT_ELASTIC_TITLE
$-----+-----+-----+-----+-----+
Sphere Projectile
$-----+-----+-----+-----+-----+
$#      mid      ro      e      pr      da      db      not used
      &MIDP      &ROP      &EP      &PRP
$-----+-----+-----+-----+-----+
*MAT_COMPOSITE_DMG_MSC_TITLE
$-----+-----+-----+-----+-----+
PW S-2 Glass/SC-15 0 Layer with beta = 0
$-----+-----+-----+-----+-----+
$#      mid      ro      ea      eb      ec      prba      prca      prcb
      &MID101    &DENSITY    &E11      &E22      &E33      &NU21      &NU31      &NU32
$#      gab      gbc      gca      aopt      macf
      &G12      &G23      &G31      2.0      0
$#      xp      yp      zp      a1      a2      a3
      0.000    0.000    0.000    1.000    0.000    0.000
$#      v1      v2      v3      d1      d2      d3      beta
      0.000    0.000    0.000    0.000    1.000    0.000    &BETA101
$#      sat      sac      sbt      sbc      sct      sfc      sfs      sab
      &X1T      &X1C      &X2T      &X2C      &X3T      &SFC      &SFS      &S12
$#      sbc      sca      sffc      amodel      phic      e_limt      s_delm
      &S23      &S31      &SFFC      2.0      &PHIC      &ELIMIT      &SDELAM
```

```
$#      omgm      ecrsh      eexpn      cr1/sig      aml/fda
      &OMGMX      &ECRSH      &EEXPX      &CR1SIG      &AM1FD1
$# am2/fdb am3/sfc/s am4/mc/de cr2/ea/eb cr3/g cr4/ec
      &AM2FD2      &AM3FCPS      &AM4MCDE      &CR2E1E2      &CR3G      &CR4E3
$-----+-----+-----+-----+-----+-----+-----+-----+
*MAT_COMPOSITE DMG MSC TITLE
$-----+-----+-----+-----+-----+-----+-----+-----+
PW S-2 Glass/SC-15 0 Layer with beta = 90
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      mid      ro      ea      eb      ec      prba      prca      prcb
      &MID102      &DENSITY      &E11      &E22      &E33      &NU21      &NU31      &NU32
$#      gab      gbc      gca      aopt      macf
      &G12      &G23      &G31      2.0      0
$#      xp      yp      zp      a1      a2      a3
      0.000      0.000      0.000      1.000      0.000      0.000
$#      v1      v2      v3      d1      d2      d3      beta
      0.000      0.000      0.000      0.000      1.000      0.000      &BETA102
$#      sat      sac      sbt      sbc      sct      sfc      sfs      sab
      &X1T      &X1C      &X2T      &X2C      &X3T      &SFC      &SFS      &S12
$#      sbc      sca      sffc      amodel      phic      e_limt      s_delm
      &S23      &S31      &SFFC      2.0      &PHIC      &ELIMIT      &SDELAM
$#      omgm      ecrsh      eexpn      cr1/sig      aml/fda
      &OMGMX      &ECRSH      &EEXPX      &CR1SIG      &AM1FD1
$# am2/fdb am3/sfc/s am4/mc/de cr2/ea/eb cr3/g cr4/ec
      &AM2FD2      &AM3FCPS      &AM4MCDE      &CR2E1E2      &CR3G      &CR4E3
$-----+-----+-----+-----+-----+-----+-----+-----+
$ *** END OF PARAMETER EXPRESSIONS ***
$-----+-----+-----+-----+-----+-----+-----+-----+
*INCLUDE
$-----+-----+-----+-----+-----+-----+-----+-----+
002-contact-SMP.key
$-----+-----+-----+-----+-----+-----+-----+-----+
*INCLUDE
$-----+-----+-----+-----+-----+-----+-----+-----+
$# Use any one of the following FILES with corresponding SPC file
$# The First FILE has a total of 40x40x4=6400 Elements
$# The Second FILE has a total of 80x80x10=64000
$-----+-----+-----+-----+-----+-----+-----+-----+
$# 003-101-102-80mmx80mmx2mm-Composite-Plate-FEM.key
003-101-102-80mmx80mmx2mm-Composite-Plate-FINE-FEM.key
$-----+-----+-----+-----+-----+-----+-----+-----+
*INCLUDE
$-----+-----+-----+-----+-----+-----+-----+-----+
$# 005-1000-SPC.key
005-1000-FINE-SPC.key
$-----+-----+-----+-----+-----+-----+-----+-----+
*INCLUDE
$-----+-----+-----+-----+-----+-----+-----+-----+
004-700-Sphere-FEM.key
$-----+-----+-----+-----+-----+-----+-----+-----+
*PART_MOVE
$-----+-----+-----+-----+-----+-----+-----+-----+
$      pid      xmov      ymov      zmov      cid
      700      &dx      &dy      &dz
$-----+-----+-----+-----+-----+-----+-----+-----+
*CONTROL_ENERGY
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      hgen      rwen      slnten      rylen
      2      2      2      2
$-----+-----+-----+-----+-----+-----+-----+-----+
*CONTROL_HOURLASS
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      ihq      qh
      7      0.100000
$-----+-----+-----+-----+-----+-----+-----+-----+
*CONTROL_OUTPUT
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      npopt      neecho      nrefup      iaccop      opifs      ipnint      ikedit      iflush
      0      0      0      0      0.000      0      100      100
$#      ipttf      ierode      tet10      msgmax      ipcurv
```

```

      0      1      2      50
$-----+-----+-----+-----+-----+-----+-----+
*CONTROL_TERMINATION
$-----+-----+-----+-----+-----+-----+-----+
$#  endtim    endcyc    dtmin    endeng    endmas
    &ENDTIME
$-----+-----+-----+-----+-----+-----+-----+
*CONTROL_TIMESTEP
$-----+-----+-----+-----+-----+-----+-----+
$#  dtinit    tssfacc    isdo    tslimt    dt2ms    lctm    erode    ms1st
    0.000      &TSSFAC
$#  dt2msf    dt2mslc    imsc1
    0.000      0      0
$-----+-----+-----+-----+-----+-----+-----+
*DATABASE_GLSTAT
$-----+-----+-----+-----+-----+-----+-----+
$#  dt    binary    lcur    ioopt    dthff    binhf
    &DTBIN      3
$-----+-----+-----+-----+-----+-----+-----+
*DATABASE_MATSUM
$-----+-----+-----+-----+-----+-----+-----+
$#  dt    binary    lcur    ioopt    dthff    binhf
    &DTBIN      3
$-----+-----+-----+-----+-----+-----+-----+
*DATABASE_RCFORC
$-----+-----+-----+-----+-----+-----+-----+
$#  dt    binary    lcur    ioopt    dthff    binhf
    &DTBIN      3
$-----+-----+-----+-----+-----+-----+-----+
*DATABASE_BINARY_D3PLOT
$-----+-----+-----+-----+-----+-----+-----+
$#  dt    lcdt    beam    npltc
    &DTD3      0
$#  ioopt
    0
$-----+-----+-----+-----+-----+-----+-----+
*DATABASE_EXTENT_BINARY
$-----+-----+-----+-----+-----+-----+-----+
$#  neiph    neips    maxint    strflg    sigflg    epsflg    rltflg    engflg
    &NEIPH    &NEIPH    3      1      1      1      1      1
$#  cmpflg    ieverp    beamip    dcomp    shge    stssz    n3thdt    ialemat
    0      1      0      1      1      1      2      1
$#  nintsld    pkp_sen    sclp    unused    msscl    therm
    0      0      1.000000
$-----+-----+-----+-----+-----+-----+-----+
*CONTACT_FORCE_TRANSducer_PENALTY_ID
$-----+-----+-----+-----+-----+-----+-----+
$#  cid title
    700 Sphere Impact Force
$-----+-----+-----+-----+-----+-----+-----+
$#  ssid    msid    sstyp    mstyp    sboxid    mboxid    spr    mpr
    700      3
$#  fs    fd    dc    vc    vdc    penchk    bt    dt
    0.000    0.000    0.000    0.000    0.000    0      0.000    1.00E+20
$#  sfs    sfm    sst    mst    sfst    sfmt    fsf    vsf
    0.000000    0.000000    0.000    0.000    0.000000    0.000000    0.000000    0.000000
$-----+-----+-----+-----+-----+-----+-----+
*SET_PART_LIST
$-----+-----+-----+-----+-----+-----+-----+
$#  sid    da1    da2    da3    da4
    123
$#  pid1    pid2    pid3    pid4    pid5    pid6    pid7    pid8
    101    102    700
$-----+-----+-----+-----+-----+-----+-----+
*SET_PART_LIST
$-----+-----+-----+-----+-----+-----+-----+
$#  sid    da1    da2    da3    da4
    700
$#  pid1    pid2    pid3    pid4    pid5    pid6    pid7    pid8
    700
```

```
$-----+-----+-----+-----+-----+-----+-----+-----+
*PART
$-----+-----+-----+-----+-----+-----+-----+-----+
Composite Layer 1 TOP
$#      pid      secid      mid      eosid      hgid      grav      adpopt      tmid
      101        100        101
$-----+-----+-----+-----+-----+-----+-----+-----+
*PART
$-----+-----+-----+-----+-----+-----+-----+-----+
Composite Layer 2 BOTTOM
$#      pid      secid      mid      eosid      hgid      grav      adpopt      tmid
      102        100        102
$-----+-----+-----+-----+-----+-----+-----+-----+
*PART
$-----+-----+-----+-----+-----+-----+-----+-----+
Sphere Projectile
$#      pid      secid      mid      eosid      hgid      grav      adpopt      tmid
      700        100        700
$-----+-----+-----+-----+-----+-----+-----+-----+
*SECTION_SOLID
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      secid      elform      aet
      100          1
$-----+-----+-----+-----+-----+-----+-----+-----+
*INITIAL_VELOCITY_GENERATION
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      id      styp      omega      vx      vy      vz      ivtan
      700          2      0.0      &VX      &VY      &VZ          0
$      xc      yc      zc      nx      ny      nz      phase
$-----+-----+-----+-----+-----+-----+-----+-----+
*END
$-----+-----+-----+-----+-----+-----+-----+-----+
```

**FILE: 002-contact-SMP.key**

```
$-----+-----+-----+-----+-----+-----+-----+-----+
*KEYWORD
$-----+-----+-----+-----+-----+-----+-----+-----+
*CONTROL_CONTACT
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      slsfac      rwpnal      islchk      shlthk      penopt      thkchg      orien      enmass
      &SLSFAC      0.000          1          0          0          0          1          1
$#      usrstr      usrfrc      nsbcs      interm      xpene      ssthk      ecdt      tiedprj
      0          0      &BSORT          0      4.000000
$#      sfric      dfrc      edc      vfc      th      th_sf      pen_sf
      0.000      0.000      0.000      0.000      0.000      0.000      0.000
$#      ignore      frceng      skiprwg      outseg      spotstp      spotdel      spothin
      1          0          0          0          0          0          0.000
$#      isym      nserod      rwgaps      rwgdt      rwksf      icov      x      ithoff
      1          0          0          0.000      1.000000          0      1.000000
$-----+-----+-----+-----+-----+-----+-----+-----+
*CONTACT_ERODING_SINGLE_SURFACE
$-----+-----+-----+-----+-----+-----+-----+-----+
$#      ssid      msid      sstyp      mstyp      sboxid      mboxid      spr      mpr
      123          2
$#      fs      fd      dc      vc      vdc      penchk      bt      dt
      0.500      0.300      0.000      0.000      20.00          0          0.00      1.00E+28
$#      sfs      sfm      sst      mst      sfst      sfmt      fsf      vsf
      1.000000      1.000000      0.000      0.000      0.000000      0.000000      0.000000      0.000000
$#      isym      erosop      iadj
      0          1          1
$#      soft      sofsc1      lcidab      maxpar      sbopt      depth      bsort      frcfrq
      2      &SLSFAC          0      &PARMAX      &SBOPT      &DEPTH      &BSORT          1
$#      penmax      thkopt      shlthk      snlog      isym      i2d3d      sldthk      sldstf
      0          1      &SLDTHK          0.000
$#      igap      ignore      dprfac      dtstif      unused      unused      flangl
      1          1
$-----+-----+-----+-----+-----+-----+-----+-----+
*END
$-----+-----+-----+-----+-----+-----+-----+-----+
```



**FILE: 003-101-102-80mmx80mmx2mm-Composite-Plate-FEM.key**

This file contains the \*NODE & \*ELEMENT\_SOLID cards for the composite parts 101 and 102.

**FILE: 004-700-Sphere-FEM.key**

This file contains the \*NODE & \*ELEMENT\_SOLID cards for the Steel sphere part 700.

**FILE: 005-1000-SPC.key**

```
$-----+-----+-----+-----+-----+-----+-----+-----+
*KEYWORD
$-----+-----+-----+-----+-----+-----+-----+-----+
*BOUNDARY_SPC_SET
$#      nsid      cid      dofx      dofy      dofz      dofrx      dofry      dofrz
      1000         0         1         1         1         1         1         1
*SET_NODE_LIST_TITLE
Edge Fixed SPC
$#      sid      da1      da2      da3      da4      solver
      1000      0.000      0.000      0.000      0.000MECH
$#      nid1      nid2      nid3      nid4      nid5      nid6      nid7      nid8
      1000001      1000002      1000003      1000004      1000005      1000006      1000007      1000008
      1000009      1000010      1000011      1000012      1000013      1000014      1000015      1000016
.
.
.
      1008390      1008391      1008392      1008393      1008394      1008395      1008396      1008397
      1008398      1008399      1008400      1008401      1008402      1008403      1008404      1008405
$-----+-----+-----+-----+-----+-----+-----+-----+
*END
$-----+-----+-----+-----+-----+-----+-----+-----+
```


**RUNNING A LARGER MODEL**

Above files runs a smaller model with  $40 \times 40 \times 4 = 6400$  elements for the composite plate. There are two additional files that will run a larger model with  $80 \times 80 \times 10 = 64000$  elements for the composite plate. Name of these two files are as follows:


**003-101-102-80mmx80mmx2mm-Composite-Plate-FINE-FEM.key****005-1000-FINE-SPC.key**

## RESULTS AND DISCUSSION

### Deformation as a Function of Time

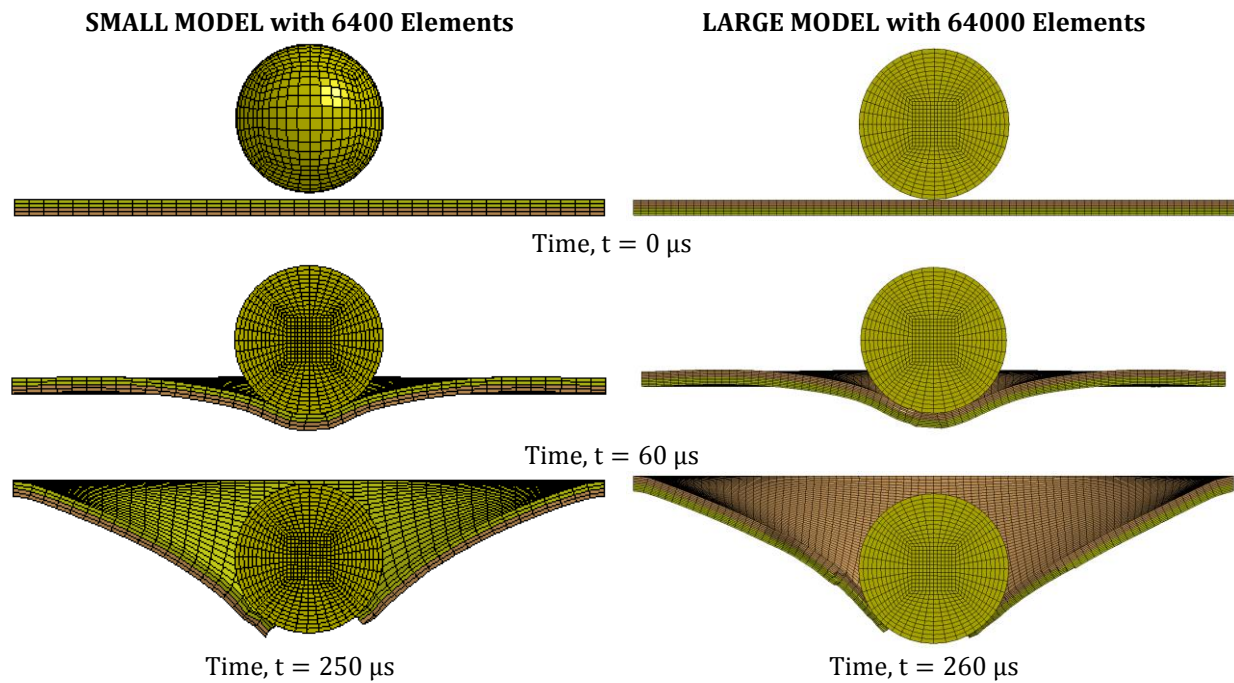


### Contour of History Variable # 7, Fiber Tension-Shear Damage Mode along A

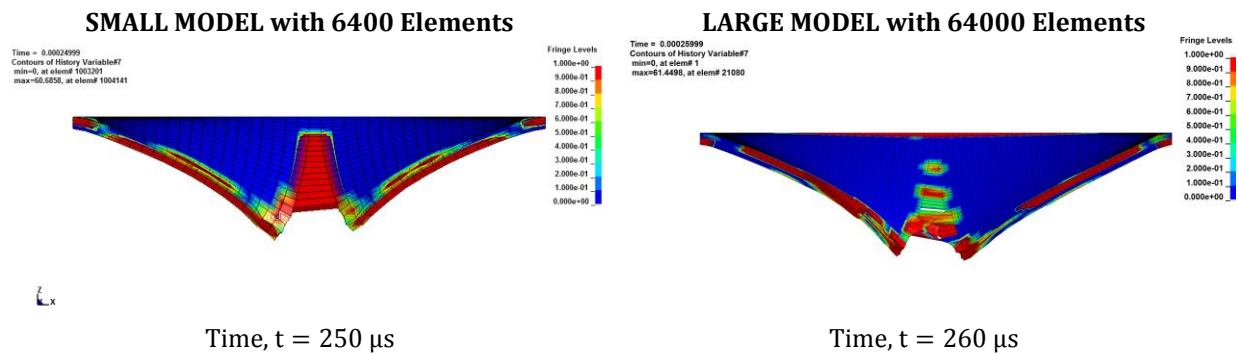

## Contour of History Variable # 8, Fiber Tension-Shear Damage Mode along B

SMALL MODEL with 6400 Elements

Time = 0.00028999  
Contours of History Variable#8  
min=0, at elem# 1003201  
max=60.9619, at elem# 1000901

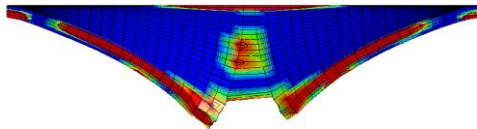


Fringe Levels  
1.000e+00  
9.000e-01  
8.000e-01  
7.000e-01  
6.000e-01  
5.000e-01  
4.000e-01  
3.000e-01  
2.000e-01  
1.000e-01  
0.000e+00

Time,  $t = 250 \mu s$

LARGE MODEL with 64000 Elements

Time = 0.00028999  
Contours of History Variable#8  
min=0, at elem# 1  
max=62.8476, at elem# 42650

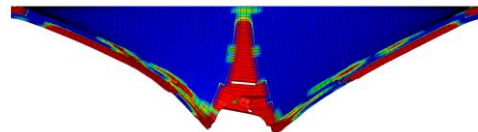


Fringe Levels  
1.000e+00  
9.000e-01  
8.000e-01  
7.000e-01  
6.000e-01  
5.000e-01  
4.000e-01  
3.000e-01  
2.000e-01  
1.000e-01  
0.000e+00

Time,  $t = 260 \mu s$

## Contour of History Variable # 9, Fiber Crush Damage Mode

SMALL MODEL with 6400 Elements

Time = 0.00028999  
Contours of History Variable#9  
min=0, at elem# 1003201  
max=3.72916, at elem# 1004020

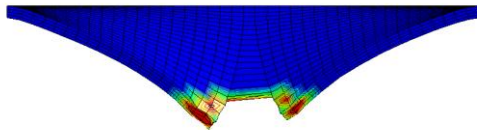


Fringe Levels  
1.000e+00  
9.000e-01  
8.000e-01  
7.000e-01  
6.000e-01  
5.000e-01  
4.000e-01  
3.000e-01  
2.000e-01  
1.000e-01  
0.000e+00

Time,  $t = 250 \mu s$

LARGE MODEL with 64000 Elements

Time = 0.00028999  
Contours of History Variable#9  
min=0, at elem# 1  
max=19.4766, at elem# 28758

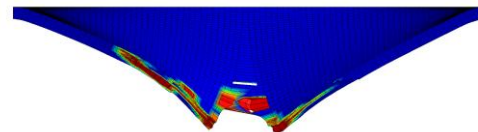


Fringe Levels  
1.000e+00  
9.000e-01  
8.000e-01  
7.000e-01  
6.000e-01  
5.000e-01  
4.000e-01  
3.000e-01  
2.000e-01  
1.000e-01  
0.000e+00

Time,  $t = 260 \mu s$

## Contour of History Variable # 10, In-Plane Matrix Damage Mode

**SMALL MODEL with 6400 Elements**


Time = 0.00028999  
Contours of History Variable#10  
min=0, at element# 1003201  
max=66.8858, at element# 1004141

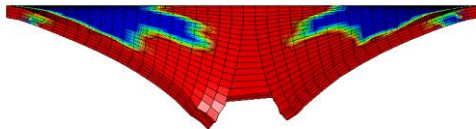

Time,  $t = 250 \mu s$

**LARGE MODEL with 64000 Elements**

Time = 0.00028999  
Contours of History Variable#10  
min=0, at element# 1  
max=66.8166, at element# 60921

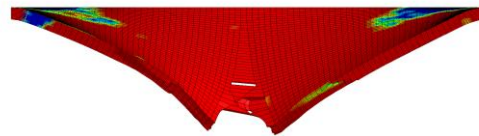


Time,  $t = 260 \mu s$

## Contour of History Variable # 11, Transverse Matrix Damage Mode

**SMALL MODEL with 6400 Elements**


Time = 0.00028999  
Contours of History Variable#11  
min=0, at element# 1003201  
max=57.9238, at element# 1004020

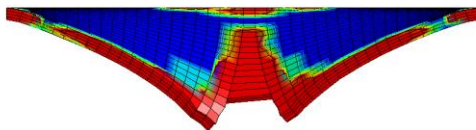

Time,  $t = 250 \mu s$

**LARGE MODEL with 64000 Elements**


Time = 0.00028999  
Contours of History Variable#11  
min=0, at element# 1  
max=100000, at element# 16119

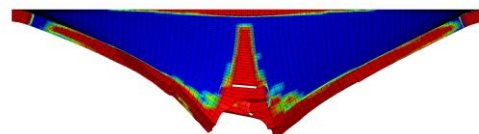

Time,  $t = 260 \mu s$

## Contour of History Variable # 12, Delamination Damage Mode

**SMALL MODEL with 6400 Elements**

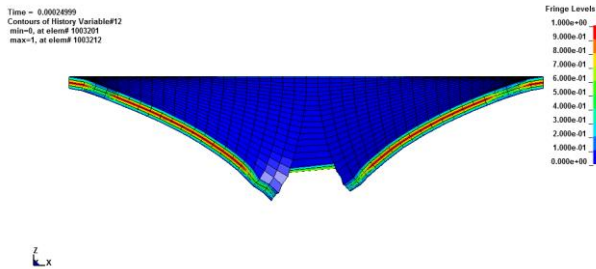

Time, t = 250  $\mu$ s


**LARGE MODEL with 64000 Elements**




Time, t = 260  $\mu$ s

## Time History of Impact-Contact Force

**SMALL MODEL with 6400 Elements**

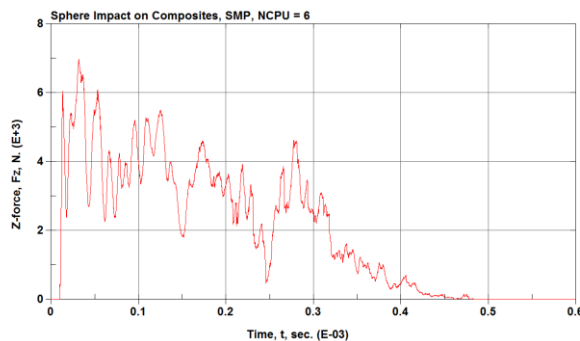

**LARGE MODEL with 64000 Elements**

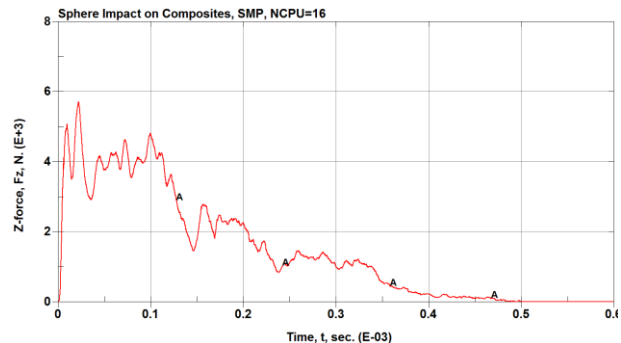

This example problem can be downloaded from UD-CCM MAT162 website:

<http://www.ccm.udel.edu/software/mat162/>

### EXAMPLE 1: Sphere-Impact-on-Composites-SOLID-MAT162.zip

This zip folder contains the following KEYWORD files. Run the first file.

001-Sphere-Impact-on-Composite-Plate.key

002-contact-SMP.key

003-101-102-80mmx80mmx2mm-Composite-Plate-FEM.key

003-101-102-80mmx80mmx2mm-Composite-Plate-FINE-FEM.key

004-700-Sphere-FEM.key

005-1000-FINE-SPC.key

005-1000-SPC.key

This Page is Intentionally Left Blank


## EXAMPLE 2: SPHERE IMPACT ON COMPOSITE SHELLS & SOLIDS

### Comparing Composite Damage Modeling with MAT-162 and MAT-054


MAT162 is a rate dependent progressive composite damage model for solid elements. In composite shell elements, transverse shear damage cannot be defined and this is why a composite solid element defining transverse shear damage is essential in modeling problems where transverse shear damage is important. Shell elements are efficient for thin-section composites, whereas thick-section composites can be modeled using multiple through-thickness elements. MAT162 for solid elements have unique quadratic progressive damage modes, which no other material model offers. These unique damage modes, such as, (i) Tension-Shear, (ii) Axial Compression, (iii) Inter laminar Shear (ILS) and Delamination, (iv) Fiber Shear (FS) or Punch Shear (PS), and (v) Fiber Crush provides the theoretical framework for modeling most known composite damages.

Benefits of MAT162 progressive damage can be elucidated with simple examples. Consider the transverse impact of a 20mm sphere with an impact velocity of 50 m/s on an 80mm x 80mm x 2mm composite plate modeled with perfectly clamped boundary condition. Shell elements with MAT054 and solid elements with MAT162 damage predictions shows that MAT054 can only model in-plane tension and compression damage, while MAT162 can predict tension-shear along direction 1 & 2, in-plane shear, transverse shear and associated delamination.

Damage Modes: Shell Elements – MAT054

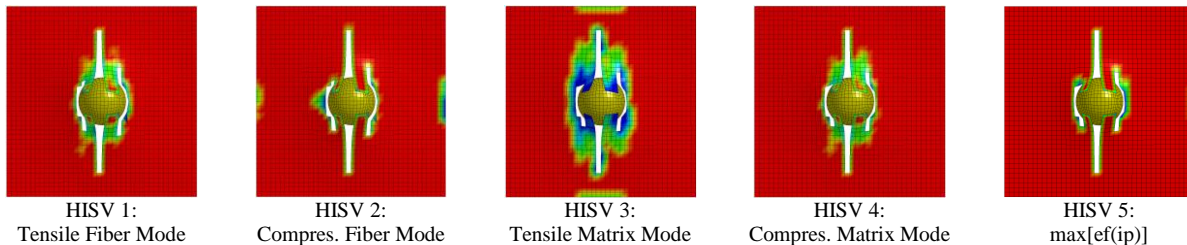

Damage Modes: Solid Elements – MAT162

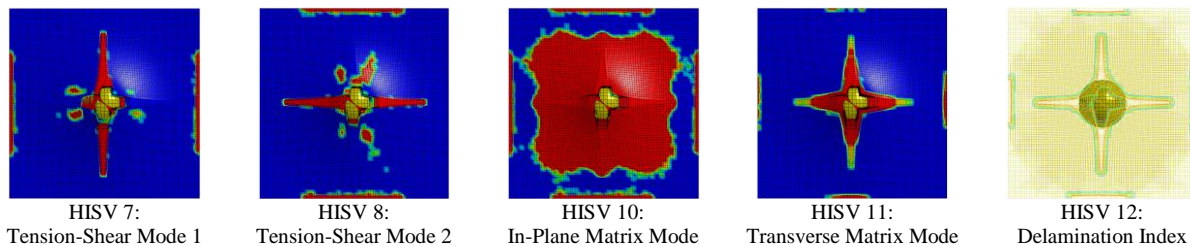

In modeling out-of-plane deformation of any kind, the primary damage mode is tension-shear where MAT162 defines a quadratic damage function with in-plane tension and out-of-plane shear properties for the initiation of tension-shear damage.



$$f_7 = \left\{ \frac{E_1 \langle \varepsilon_1 \rangle}{X_1^T} \right\}^2 + \left\{ \frac{G_{31} \varepsilon_{31}}{S_1^{FS}} \right\}^2$$

The MAT054 equivalent damage function uses in-plane tension and in-plane shear properties instead, and in general fails to account for transverse shear deformation.

$$e_f = \left\{ \frac{E_1 \varepsilon_1}{X_1^T} \right\}^2 + \beta \left\{ \frac{G_{12} \varepsilon_{12}}{S_{12}} \right\}^2$$

The inability of MAT54 in modeling transverse damage modes greatly affects the impact-contact force and associated work done, predicts premature perforation while MAT162 predicts partial perforation and complete rebound of the sphere in case of initial impact velocity of 50 m/s.

#### Quantitative Comparison between MAT054 (Shell) & MAT162 (Solid) Material Models

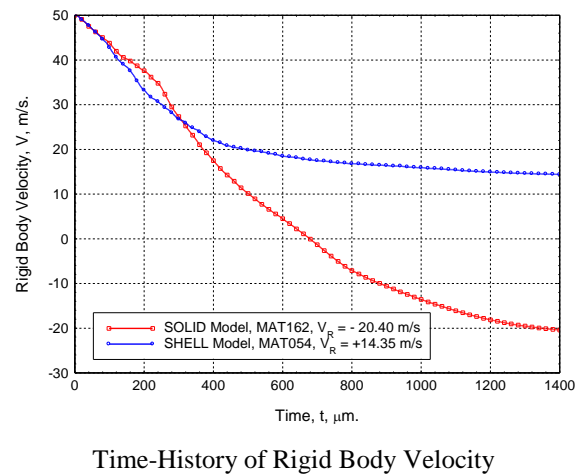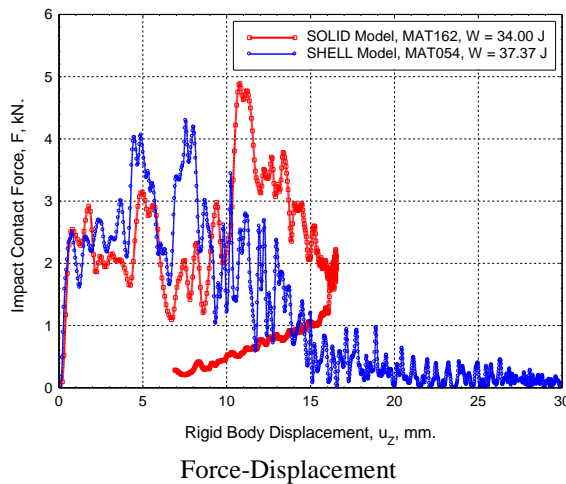

A local MAT162 solid model in the anticipated damage region combined with global shell elements can be used to efficiently and accurately model large-scale impact application such as, crash analysis of automotive composite components and aerospace structures under impact conditions.

This example problem can be downloaded from UD-CCM MAT162 website:

<http://www.ccm.udel.edu/software/mat162/>

#### EXAMPLE 1: Sphere-Impact-on-Composites-SOLID-MAT162.zip

This zip folder contains the following KEYWORD files. Run the first file.

```
001-Sphere-Impact-on-Composite-Plate.key
002-contact-SMP.key
003-101-102-80mmx80mmx2mm-Composite-Plate-FEM.key
003-101-102-80mmx80mmx2mm-Composite-Plate-FINE-FEM.key
004-700-Sphere-FEM.key
005-1000-FINE-SPC.key
005-1000-SPC.key
```



**EXAMPLE 2: Sphere-Impact-on-Composites-SHELL-MAT54.zip**

This zip folder contains the following KEYWORD files. Run the first file.

001-Sphere-Impact-on-Composite-Shell.key  
002-control-cards.key  
003-Shell-Plate-80mm-x-80-mm-FEM.key  
004-700-Sphere-FEM.key  
005-parts-partsets-sections-materials-FEM.key  
006-100-Node-SET.key  
006-nodeset-elementset-segmentset-FEM.key  
007-contact-single-surface.key  
008-boundary-conditions.key  
009-initial-conditions.key  
010-loading-conditions.key  
011-output-database.key

